



Yandal Gold Project, Western Australia – Exploration Update

**FURTHER HIGH-GRADE EXTENSIONAL RESULTS CONFIRM GROWING  
POTENTIAL OF THE HORSEWELL GOLD CAMP**

*Latest assays including 12m @ 5.4g/t and 18.5m @ 1.7g/t to feed into resource update in Q2 2025*

**Highlights:**

Bronco Gold Deposit

High-grade plunging shoots successfully delineated within the broader mineralised shear zone by drilling at a revised orientation:

- HWDD041: 18.5 metres @ 1.7g/t Au from 81 metres (including 3.2 metres @ 8.0g/t Au)

Mineralisation at the Konik lode extended 100 metres along strike to the north-west by step-out drilling:

- HWRC336: 16.0 metres @ 1.2g/t Au from 146 metres (including 3.0 metres @ 4.6g/t Au)

Bronco continues to represent a bulk-tonnage target below the high-grade oxide mineralisation:

- HWDD038: 62.3 metres @ 0.9g/t Au from 114 metres (including 3.1 metres @ 3.0g/t Au)

Marwari Gold Deposit

Significant high-grade mineralisation intersected in RC drilling at Marwari, confirming the revised orientation of the mineralisation:

- HWRC283: 12.0 metres @ 5.4g/t Au from 108m (including 4.0 metres @ 8.4g/t Au)

Mineralisation extended a further 260 metres north along strike from the Marwari Gold Deposit by step-out RC drilling:

- HWRC287: 28.0 metres @ 1.0g/t Au from 16m (including 4.0 metres @ 3.8g/t Au)

Gold mineralisation along the Marwari Trend now exceeds 1.6 kilometres in strike length and remains predominantly untested.

- 2024 drilling now completed within the limits of current heritage clearances, allowing Strickland to undertake a detailed review and interpretation of drilling data and commence resource evaluation.

- Updated Mineral Resource Estimate (MRE) for the Yandal Gold Project due in Q2 2025, with ~20,000m of discovery and growth-focused drilling planned next year to drive further resource growth.

**Introduction**

Strickland Metals Limited (ASX: STK) (**Strickland** or the **Company**) is pleased to provide an update on exploration activities at the Horse Well Gold Camp, part of the Company's 100%-owned Yandal Gold Project in Western Australia.

Drilling at the Horse Well Gold Camp continues to delineate extensions to mineralisation both along strike and at depth, with further significant results received from drilling at the Bronco and Marwari Gold Deposits (Figure 1).

For personal use only



Paul L’Herpinere, Managing Director of Strickland, said: “These latest assays from our 2024 drilling campaign continue to build the picture of a camp-scale gold system with exciting growth potential at Horse Well. Step-out drilling continues to intersect significant gold mineralisation at both the Bronco and Marwari deposits, with our new interpretation of the orientation of the mineralised lodes helping to refine our drilling approach.

“Strickland has completed around 20,000m of focused RC and diamond drilling at Horse Well during 2024, with drilling now completed within the limits of our current heritage clearances.

“This provides us with an opportunity to pause drilling, step back and commence work on detailed interpretation of all the drilling data while also commencing work on an updated MRE. This work is now well and truly underway and will pave the way for an updated MRE in Q2 2025.

“The data gained from the 2024 program will also be invaluable in helping us to plan the next phase of drilling commencing in early 2025, where we have budgeted for another 20,000 metres to help drive further resource growth.

“These results continue to reinforce the significant potential of the Horse Well Gold Camp, and our broader Yandal Project, as an exciting growth and value creation opportunity in the heart of one WA’s premier gold mining districts, right on the doorstep of Northern Star’s Jundee gold mine.”

For personal use only

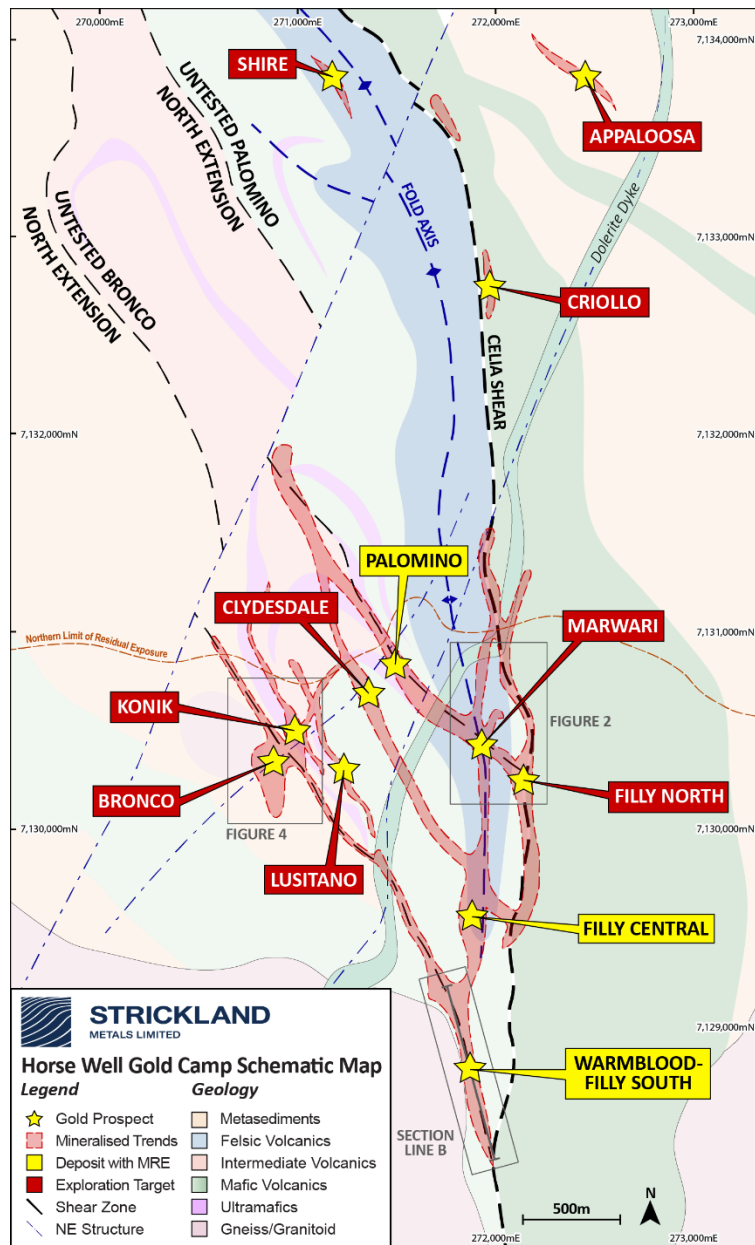


Figure 1: Schematic geological interpretation of the Horse Well Gold Camp.



## Marwari Gold Deposit

Marwari was initially discovered in 2023 by Strickland through aircore drilling across the Horse Well Gold Camp (HWAC1472: 31.0 metres @ 5.6g/t Au from 72 metres to BOH)<sup>1</sup>. Following initial RC and diamond drilling, Strickland completed structural analysis of the drill core to delineate the controls on mineralisation within the deposit.

Recent RC drilling was planned to test the revised interpretation of gold mineralisation at the Marwari Gold Deposit and successfully intersected a down-plunge extension to the primary mineralised lode:

- HWRC283: **12.0 metres @ 5.4g/t Au** from 108 metres (including 4.0 metres @ 8.0g/t Au)

Step-out drilling was then undertaken, intersecting significant mineralisation 260m north-east along strike from Marwari:

- HWRC287: **28.0 metres @ 1.0g/t Au** from 16 metres (including 4.0 metres @ 3.8g/t Au)

The mineralised Marwari Trend now exceeds a strike length of 1.6 kilometres and remains open at depth and along strike to the north (Figure 2). Importantly, over half of the Marwari Trend remains untested by RC and diamond drilling, representing a significant mineralised trend for future exploration and additional gold discoveries within the Horse Well Gold Camp.

For personal use only

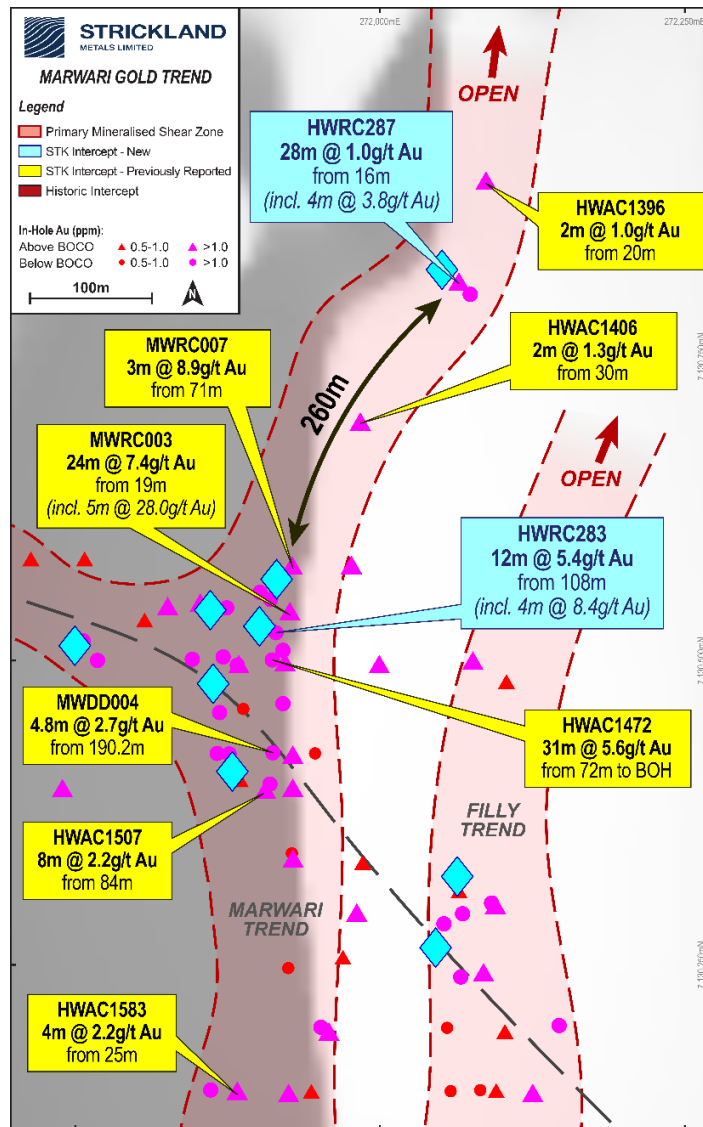


Figure 2: Marwari Trend topographic image displaying recent exploration drill holes and the parallel Filly Trend.

<sup>1</sup>See ASX announcement dated 19 September 2023.



## Bronco Gold Deposit

Recent drilling at Bronco has focused on delineating high-grade plunging lodes, similar in style to those present at the Warmblood and Palomino Deposits. From this drilling, Strickland has defined two high-grade zones within the broad mineralised shear zone, with the highest grades present along western margin of the shear zone at the contact with felsic volcanics (Figure 3 and 4):

- HWDD041: **18.5 metres @ 1.7g/t Au** from 81 metres (including 3.2 metres @ 8.0g/t Au)

Drilling at depth further supports the interpretation that Bronco remains a promising bulk-tonnage target below the exceptionally high-grade oxide mineralisation. Mineralisation remains open at depth:

- HWDD038: **62.3 metres @ 0.9g/t Au** from 114 metres (including 3.1 metres @ 3.0g/t Au)

Additional RC drilling at Konik has successfully intersected the mineralised lode a further 100m north-west, along strike from the original Konik Discovery hole:

- HWRC336: **16.0 metres @ 1.2g/t Au** from 146 metres (including 3.0 metres @ 4.6g/t Au)

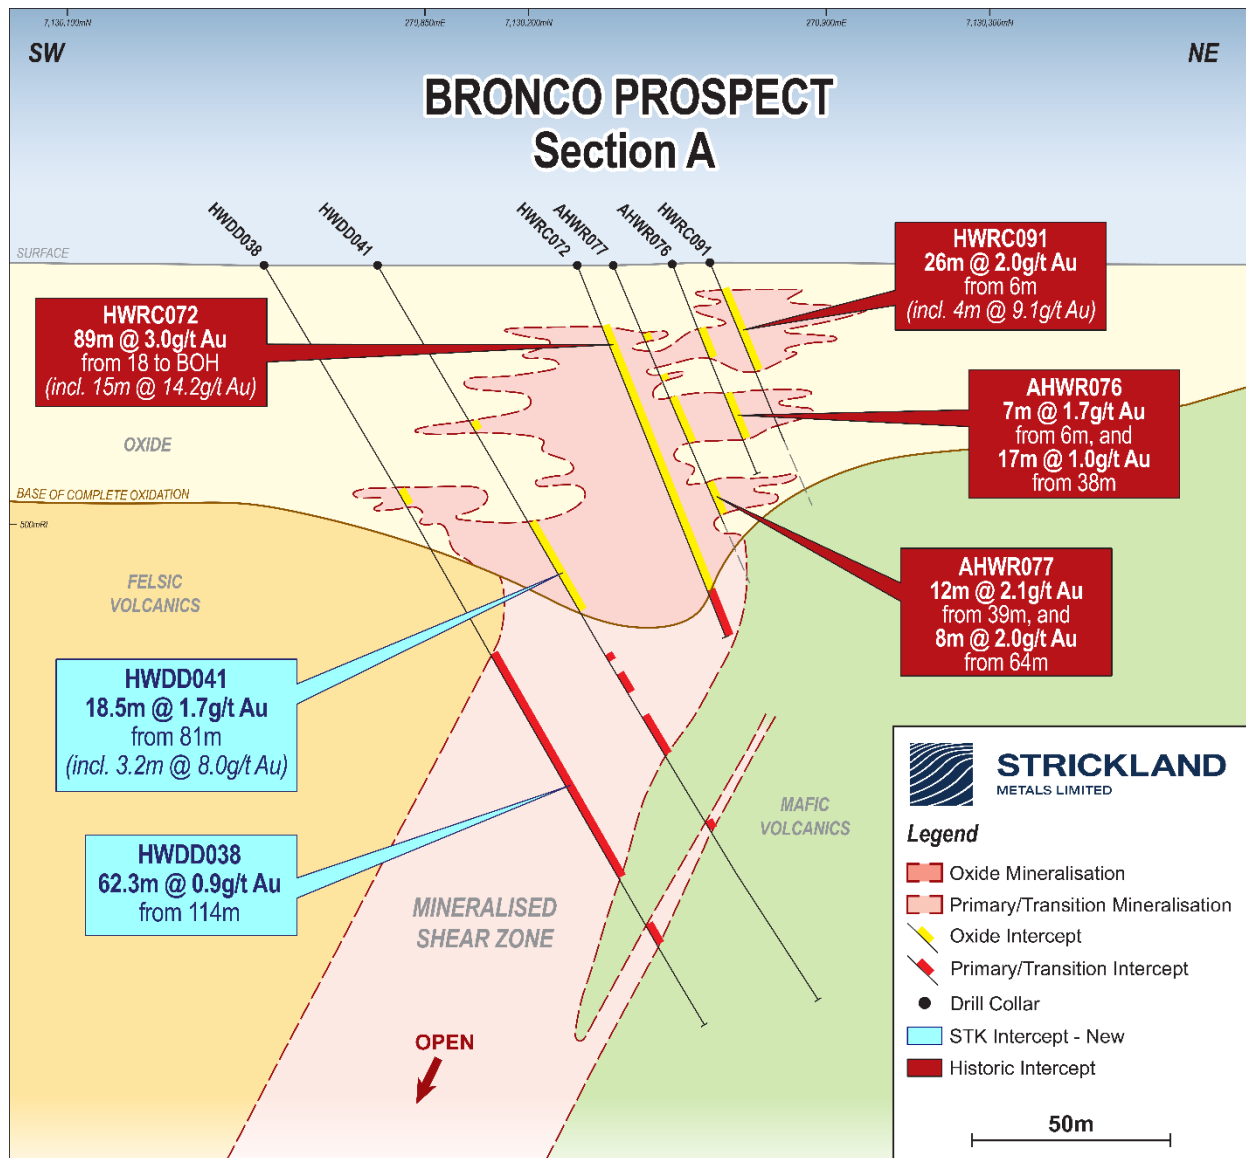


Figure 3: Cross section through the Bronco Deposit highlighting shallow high grade oxide intercepts and primary bulk potential.



For personal use only

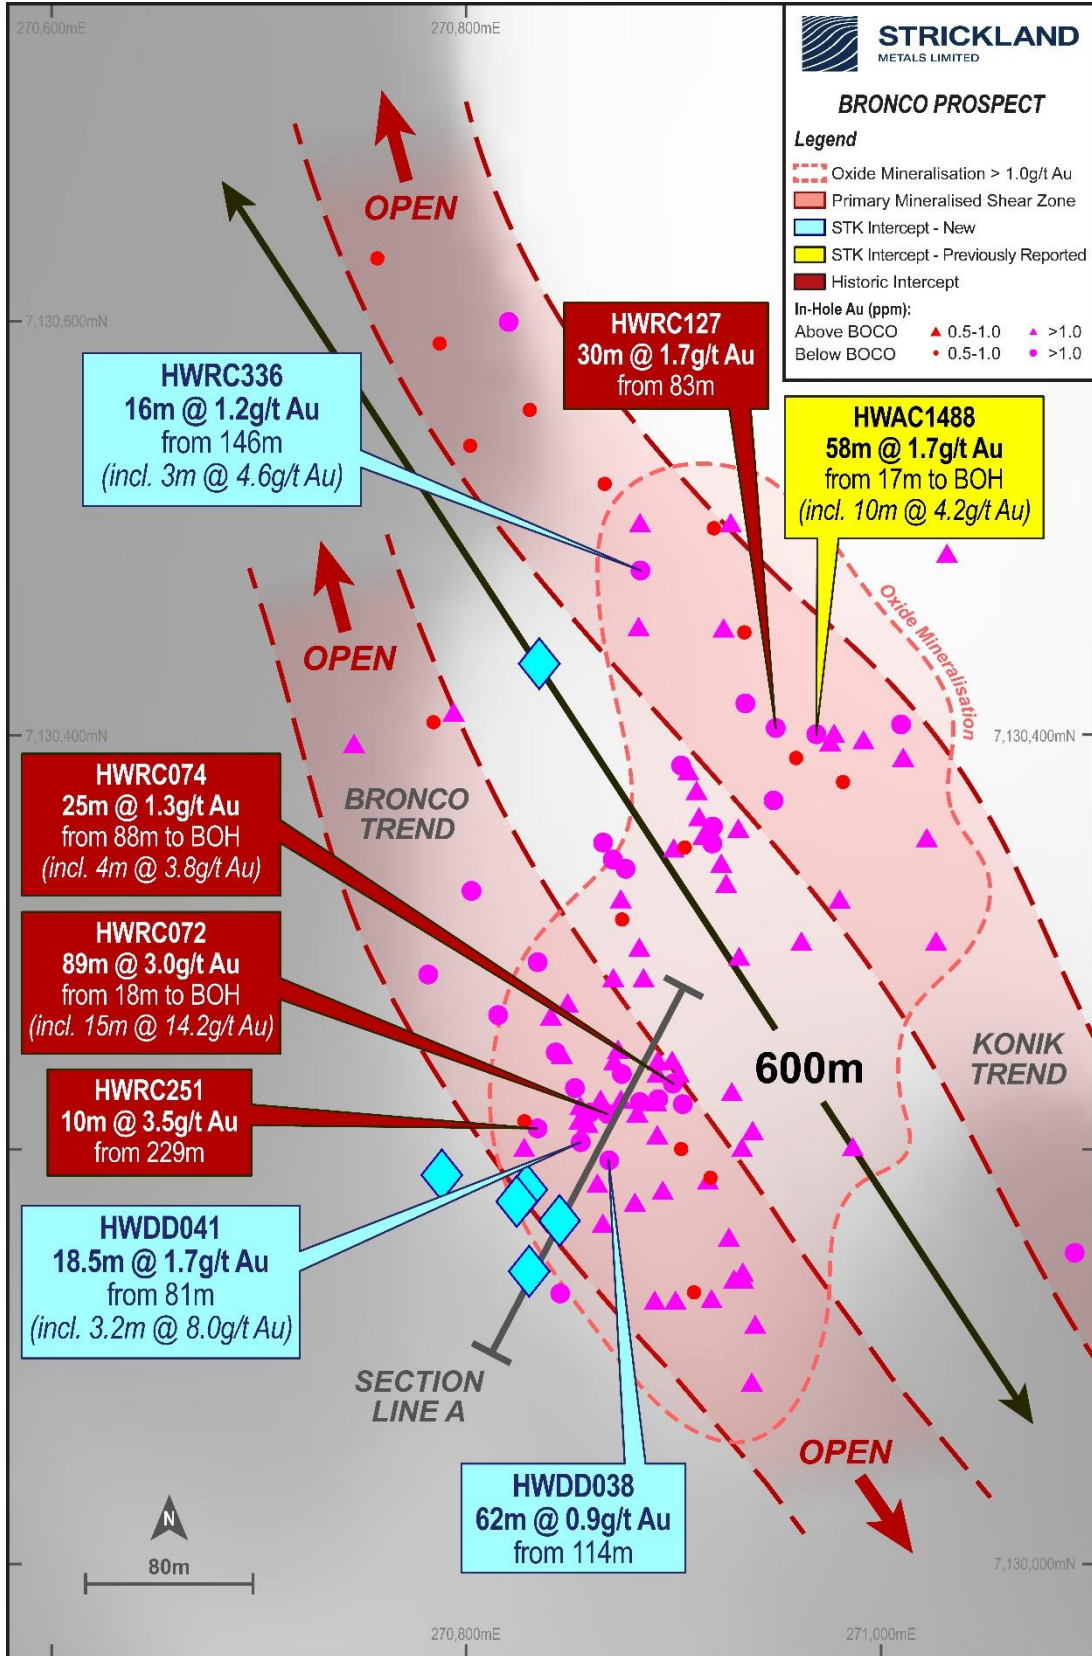


Figure 4: Bronco-Konik topographic image highlighting the extensive >1g/t Au oxide gold blanket and to two primary gold mineralised domains.



## Warmblood

Previously announced drilling by Strickland successfully delineated high-grade north-plunging mineralised lodes within the Warmblood deposit and additionally extended mineralisation across the 'Filly Gap', connecting the Warmblood and Filly South prospects into a continuous deposit with a strike of 1 kilometre (Figure 5).

The mineralisation at Warmblood remains open at depth and down-plunge to the north, with the deepest intercept in HWDD043: 5.2 metres @ 3.1g/t Au from 171.7 metres (including 2.2 metres @ 7.0g/t Au), and 7.4 metres @ 1.1g/t Au from 203.6 metres.<sup>2</sup>

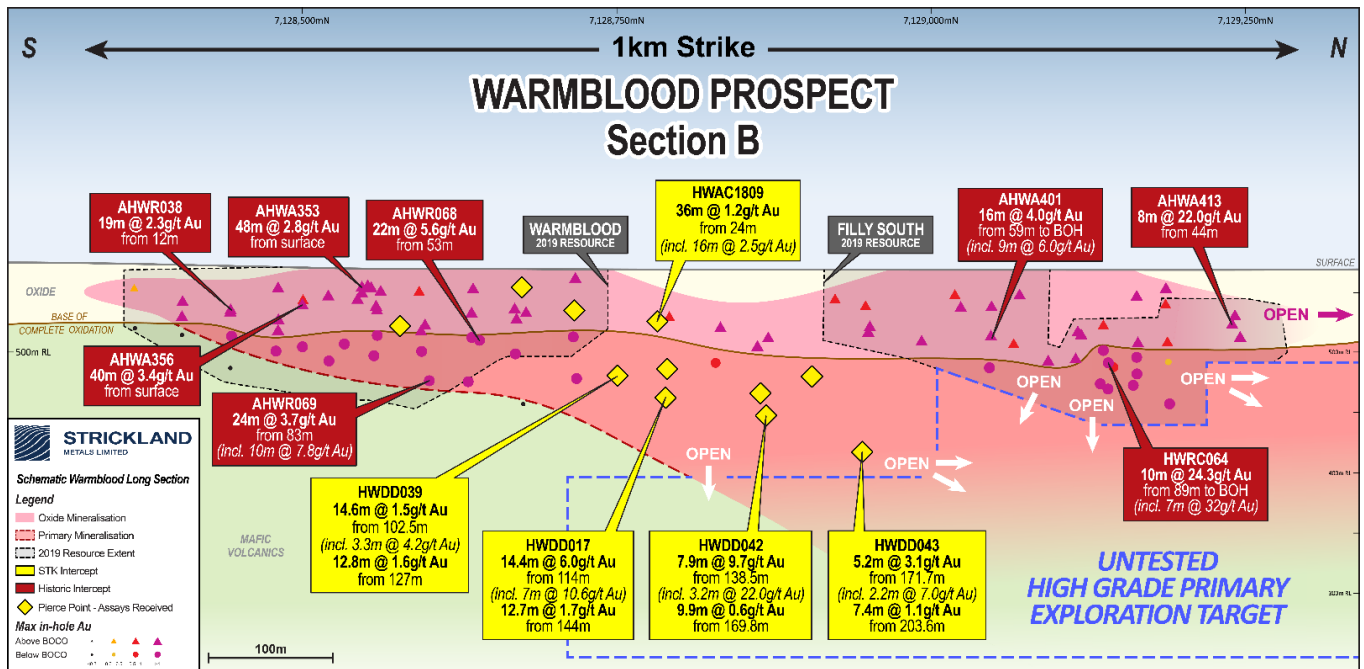


Figure 5: Warmblood Long Section highlighting Strickland's extensional drilling across the 'Filly Gap' between the historic resources at Warmblood and Filly South.

Additional shallow drilling along strike to the north of the Warmblood-Filly system has recently been completed, targeting extensions to mineralisation below transported cover and identifying a continuation of pathfinder mineralisation (Bi-Te-W-Ag) over a strike length of 1.4 kilometres.

Significant results include:

- HWRC349: **2 metres @ 1.5g/t Au** from 94 metres, and 5 metres @ 1.9g/t Au from 150 metres
- HWRC356: **4 metres @ 1.7g/t Au** from surface (300 metres north of Filly South)

## Future Plans

Strickland has now completed all planned drilling within the limits of current heritage clearance at Horse Well and drill rigs have demobilised from site.

The Company will now proceed with detailed interpretation of the drilling results, including resource evaluation work, to determine the impact of this years' strong drilling results on the overall resource potential of the Horse Well Gold Camp. An updated MRE scheduled for release in Q2 2025.

This work will also enable the Company to commence planning for further drilling to be carried out in 2025. The recognition of the Horse Well Gold Camp being situated within a major anticline, with the majority of the prospective northern area of the current deposits being open and untested by deeper drilling, provides a clear focus for resource growth.

<sup>2</sup>Refer to ASX announcement 2 September 2024.



*This release has been authorised by the Company's Managing Director Mr Paul L'Herpinere.*

— Ends —

For further information, please contact:

**Paul L'Herpinere**

**Managing Director**

Phone: +61 (8) 6317 9875

[info@stricklandmetals.com.au](mailto:info@stricklandmetals.com.au)

[stricklandmetals.com.au](http://stricklandmetals.com.au)

**Media Inquiries:**

Nicholas Read – Read Corporate

Phone: +61 (8) 9388 1474

[info@readcorporate.com.au](mailto:info@readcorporate.com.au)

**Competent Person's Statement**

The information in this report that relates to Exploration Results is based on information compiled or reviewed by Mr Richard Pugh who is the Strickland Metals Limited Technical Director, WA and is a current Member of the Australian Institute of Geoscientists (AIG). Mr Richard Pugh has sufficient experience, which is relevant to the style of mineralisation and types of deposit under consideration and to the activities undertaken, to qualify as a Competent Person as defined in the 2012 Edition of the "Australasian Code of Reporting of Exploration Results, Mineral Resources and Ore Reserves". Mr Pugh consents to the inclusion in the report of the matters based on the information in the form and context in which it appears.

**Forward-Looking Statements**

This announcement may contain certain forward-looking statements, guidance, forecasts, estimates, prospects, projections or statements in relation to future matters that may involve risks or uncertainties and may involve significant items of subjective judgement and assumptions of future events that may or may not eventuate (Forward-Looking Statements). Forward-Looking Statements can generally be identified by the use of forward-looking words such as "anticipate", "estimates", "will", "should", "could", "may", "expects", "plans", "forecast", "target" or similar expressions and may include, without limitation, statements regarding plans, strategies and objectives of management, anticipated production and expected costs. Indications of, and guidance on future earnings, cash flows, costs, financial position and performance are also Forward Looking Statements.

Persons reading this announcement are cautioned that such statements are only predictions, and that actual future results or performance may be materially different. Forward-Looking Statements, opinions and estimates included in this announcement are based on assumptions and contingencies which are subject to change, without notice, as are statements about market and industry trends, which are based on interpretation of current market conditions. Forward-Looking Statements are provided as a general guide only and should not be relied on as a guarantee of future performance.

No representation or warranty, express or implied, is made by Strickland that any Forward-Looking Statement will be achieved or proved to be correct. Further, Strickland disclaims any intent or obligation to update or revise any Forward-Looking Statement whether as a result of new information, estimates or options, future events or results or otherwise, unless required to do so by law.

For personal use only



## Appendix A – Significant Intercepts

Table 1 – Marwari

Hole ID	Coordinates (MGA94 Zone 51)			Hole Details				Intercept Details				
	Easting (m)	Northing (m)	RL (m)	Hole Type	Azi (deg)	Dip (deg)	Total Depth (m)	Depth from (m)	Depth To (m)	Intercept Width (m)	Grade (g/t)	Grade Summary/ Comments
HWRC280	272,065	7,130,318	572	RC	110	-60	124	16	21	5	0.8	5m @ 0.8g/t Au from 16m
HWRC281	272,046	7,130,264	572	RC	110	-60	124	47	48	1	0.5	1m @ 0.5g/t Au from 47m
HWRC282	271,901	7,130,528	572	RC	110	-60	106	40	44	4	0.9	4m @ 0.9g/t Au from 40m
HWRC283	271,863	7,130,542	572	RC	110	-60	160	108	120	12	5.4	12m @ 5.4g/t Au from 108m
including								112	116	4	8.4	4m @ 8.4g/t Au from 112m
HWRC284	271,750	7,130,510	572	RC	110	-60	106	72	76	4	0.5	4m @ 0.5g/t Au from 72m
HWRC285	271,879	7,130,411	572	RC	110	-60	106	80	84	4	0.9	4m @ 0.9g/t Au from 80m
HWRC286	271,864	7,130,482	572	RC	110	-60	106	72	76	4	0.5	4m @ 0.5g/t Au from 72m
HWRC287	272,055	7,130,813	572	RC	110	-60	112	16	44	28	1	28m @ 1g/t Au from 16m
including								40	44	4	3.8	4m @ 3.8g/t Au from 40m
HWRC288	271,913	7,130,565	572	RC	110	-60	106					NSR
HWRC289	271,927	7,130,544	572	RC	270	-60	124					NSR
MWRC001*	271,950	7,130,500	572	RC	270	-60	184	44	48	4	2.7	4m @ 2.7g/t Au from 44m
and								152	154	2	1.1	2m @ 1.1g/t Au from 152m
MWRC002*	271,990	7,130,580	572	RC	270	-60	226	16	17	1	1	1m @ 1g/t Au from 16m
MWRC003*	271,950	7,130,540	572	RC	270	-60	160	19	43	24	7.4	24m @ 7.4g/t Au from 19m
and								60	61	1	1.2	1m @ 1.2g/t Au from 60m
and								69	70	1	0.8	1m @ 0.8g/t Au from 69m
and								79	80	1	0.7	1m @ 0.7g/t Au from 79m
and								141	143	2	2.3	2m @ 2.3g/t Au from 141m
MWRC004D*	271,990	7,130,540	572	RC_D DH	270	-60	258.8					NSR
MWRC005*	271,910	7,130,500	572	RC	270	-60	154	49	50	1	1.3	1m @ 1.3g/t Au from 49m
and								122	125	3	1.2	3m @ 1.2g/t Au from 122m
MWRC006*	271,910	7,130,460	572	RC	270	-60	154	69	70	1	0.5	1m @ 0.5g/t Au from 69m
and								92	93	1	0.6	1m @ 0.6g/t Au from 92m
MWRC007*	271,950	7,130,580	572	RC	270	-60	178	36	38	2	1.3	2m @ 1.3g/t Au from 36m
and								71	74	3	8.9	3m @ 8.9g/t Au from 71m
MWRC008*	271,950	7,130,420	572	RC	270	-60	244	19	20	1	1.3	1m @ 1.3g/t Au from 19m
MWRC009*	271,990	7,130,420	572	RC	270	-60	145					NSR
MWRC010*	271,950	7,130,340	572	RC	270	-60	220	2	3	1	0.8	1m @ 0.8g/t Au from 2m
and								26	27	1	1.9	1m @ 1.9g/t Au from 26m
and								32	36	4	0.5	4m @ 0.5g/t Au from 32m
MWRC011*	271,990	7,130,340	572	RC	270	-60	244	61	62	1	0.6	1m @ 0.6g/t Au from 61m
and								80	81	1	0.6	1m @ 0.6g/t Au from 80m
and								106	107	1	0.9	1m @ 0.9g/t Au from 106m
MWRC012*	271,870	7,130,510	572	RC	90	-60	124	83	86	3	6	3m @ 6g/t Au from 83m
and								102	103	1	0.6	1m @ 0.6g/t Au from 102m
MWRC013*	271,830	7,130,510	572	RC	90	-60	184					NSR
MWDD001*	271,990	7,130,500	572	DDH	270	-60	291.1	151	152	1	0.7	1m @ 0.7g/t Au from 151m





Hole ID	Coordinates (MGA94 Zone 51)			Hole Details				Intercept Details				
	Easting (m)	Northing (m)	RL (m)	Hole Type	Azi (deg)	Dip (deg)	Total Depth (m)	Depth from (m)	Depth To (m)	Intercept Width (m)	Grade (g/t)	Grade Summary/ Comments
and								216.2	218.7	2.5	1.2	2.5m @ 1.2g/t Au from 216.2m
and								231	234	3	1.5	3m @ 1.5g/t Au from 231m
and								270	271	1	0.6	1m @ 0.6g/t Au from 270m
MWDD002*								23.4	24	0.7	0.8	0.7m @ 0.8g/t Au from 23.4m
and								30	31	1	0.9	1m @ 0.9g/t Au from 30m
and	271,950	7,130,460	572	DDH	270	-60	168.5	120.5	121.9	1.5	0.7	1.5m @ 0.7g/t Au from 120.5m
and								163.5	164	0.5	4.8	0.5m @ 4.8g/t Au from 163.5m
MWDD003*								217	222	5	0.6	5m @ 0.6g/t Au from 217m
and	272,030	7,130,500	572	RC_D DH	270	-60	314.6	247.5	248.5	1	0.9	1m @ 0.9g/t Au from 247.5m
MWDD004*								116.	128.	12	0.6	12m @ 0.6g/t Au from 116m
and								190.2	195	4.8	2.7	4.8m @ 2.7g/t Au from 190.2m
and								237	238	1	0.7	1m @ 0.7g/t Au from 237m
and	272,030	7,130,420	572	RC_D DH	270	-60	302.5	239.7	241.0	1.3	1	1.3m @ 1g/t Au from 239.7m
and								258.7	263	4.3	2.2	4.3m @ 2.2g/t Au from 258.7m
and								280	282	2	2.2	2m @ 2.2g/t Au from 280m
MWDD005*								224	227	3	0.9	3m @ 0.9g/t Au from 224m
and	272,030	7,130,460	572	RC_D DH	270	-60	299	232	233	1	0.9	1m @ 0.9g/t Au from 232m
MWDD006*	272,030	7,130,540	572	RC_D DH	270	-60	304.6	292.7	293.9	1.2	1.8	1.2m @ 1.8g/t Au from 292.7m
MWDD007*								32	36	4	0.6	4m @ 0.6g/t Au from 32m
and	272,030	7,130,580	572	RC	270	-60	154	80	84	4	0.6	4m @ 0.6g/t Au from 80m
MWDD008*	271,990	7,130,460	572	RC_D DH	270	-60	248	133.6	134.3	0.6	3.2	0.6m @ 3.2g/t Au from 133.6m

\*Previously announced or historic results.

A cutoff of 0.3g/t Au was applied to each significant intercept.

For personal use only



**Table 2 – Bronco**

Hole ID	Coordinates (MGA94 Zone 51)			Hole Details				Intercept Details				
	Easting (m)	Northing (m)	RL (m)	Hole Type	Azi (deg)	Dip (deg)	Total Depth (m)	Depth from (m)	Depth To (m)	Intercept Width (m)	Grade (g/t)	Grade Summary/ Comments
HWRC259*	270,886	7,130,369	565	RC	-60	110	148	58	60	2	1.1	2m @ 1.1g/t Au from 58m
and								71	79	8	0.9	8m @ 0.9g/t Au from 71m
including								77	78	1	2.3	1m @ 2.3g/t Au from 77m
HWRC260*	270,937	7,130,393	565	RC	-60	110	166					NSR
HWRC261*	270,785	7,130,151	566	RC	-60	110	136	132	133	1	2.2	1m @ 2.2g/t Au from 132m
HWRC262*	271,023	7,130,511	565	RC	-60	110	124					NSR
HWRC267*	271,221	7,130,412	567	RC	-60	252	100	74	75	1	1.2	1m @ 1.2g/t Au from 74m
HWRC268*	271,266	7,130,322	567	RC	-60	252	124					NSR
HWRC269	270,895	7,130,369	565	RC	-60	40	166	117	118	1	0.6	1m @ 0.6g/t Au from 117m
and								130	138	8	0.7	8m @ 0.7g/t Au from 130m
including								130	131	1	1.9	1m @ 1.9g/t Au from 130m
HWRC270*	270,998	7,130,348	570	RC	-60	40	70					NSR
HWRC271*	270,877	7,130,077	571	RC	-60	40	124	73	79	6	1.1	6m @ 1.1g/t Au from 73m
including								74	76	2	2.7	2m @ 2.7g/t Au from 74m
and								82	87	5	1.0	5m @ 1g/t Au from 82m
HWRC272*	270,903	7,130,107	569	RC	-60	40	100	49	50	1	1.6	1m @ 1.6g/t Au from 49m
and								64	65	1	1.0	1m @ 1g/t Au from 64m
HWRC273*	270,928	7,130,075	570	RC	-60	40	88	23	32	9	1.3	9m @ 1.3g/t Au from 23m
including								26	29	3	3.3	3m @ 3.3g/t Au from 26m
HWRC274*	270,715	7,130,353	565	RC	-60	40	124					NSR
HWRC336	270,835	7,130,433	564	RC	-60	50	192	146	162	16	1.2	16m @ 1.2g/t Au from 146m
including								146	149	3	4.6	3m @ 4.6g/t Au from 146m
and								157	158	1	2.1	1m @ 2.1g/t Au from 157m
and								161	162	1	1.0	1m @ 1g/t Au from 161m
HWRC337	270,832	7,130,495	564	RC	-60	50	150	83	86	3	0.5	3m @ 0.5g/t Au from 83m
HWRC338	270,799	7,130,532	564	RC	-60	50	144	80	81	1	0.6	1m @ 0.6g/t Au from 80m
HWRC339	270,777	7,130,517	564	RC	-60	50	192	20	21	1	0.5	1m @ 0.5g/t Au from 20m
and								63	65	2	0.6	2m @ 0.6g/t Au from 63m
HWRC340	270,768	7,130,573	564	RC	-60	50	96					NSR
HWRC341	270,749	7,130,557	564	RC	-60	50	192	94	95	1	0.6	1m @ 0.6g/t Au from 94m
HWRC342	270,765	7,130,635	564	RC	-60	50	180					NSR
HWRC343	270,739	7,130,612	564	RC	-60	50	156	125	126	1	0.5	1m @ 0.5g/t Au from 125m
HWRC344	270,716	7,130,596	564	RC	-60	50	198	96	97	1	0.5	1m @ 0.5g/t Au from 96m
and								99	101	2	0.5	2m @ 0.5g/t Au from 99m
and									113	114	1	0.5
HWRC345	270,733	7,130,674	564	RC	-60	50	144					NSR
HWRC346	270,708	7,130,653	564	RC	-60	50	150					NSR
HWRC347	270,689	7,130,639	564	RC	-60	50	210					NSR
HWRC348	270,842	7,130,573	564	RC	-60	50	126					NSR
HWDD012*	270,864	7,130,250	565	DDH	-60	110	169.8	31	32	1	3.8	1m @ 3.8g/t Au from 31m

For personal use only



For personal use only

Hole ID	Coordinates (MGA94 Zone 51)			Hole Details				Intercept Details				
	Easting (m)	Northing (m)	RL (m)	Hole Type	Azi (deg)	Dip (deg)	Total Depth (m)	Depth from (m)	Depth To (m)	Intercept Width (m)	Grade (g/t)	Grade Summary/ Comments
and								51.4	52.6	1.2	3.1	1.2m @ 3.1g/t Au from 51.4m
and								60	66.2	6.2	2.1	6.2m @ 2.1g/t Au from 60m
including								60	62	2	5.9	2m @ 5.9g/t Au from 60m
HWDD013*	270,737	7,130,253	565	RC_DDH	-60	110	100					NSR
HWDD014*	270,826	7,130,264	565	DDH	-60	110	227.6	52	64	12	1.4	12m @ 1.4g/t Au from 52m
including								53.5	58.3	4.8	2.5	4.8m @ 2.5g/t Au from 53.5m
and								74.1	83.3	9.2	1.7	9.2m @ 1.7g/t Au from 74.1m
including								74.1	76	1.9	4.9	1.9m @ 4.9g/t Au from 74.1m
and							99	100	1	1.4	1m @ 1.4g/t Au from 99m	
HWDD015*	270,699	7,130,267	565	RC_DDH	-60	110	148					NSR
HWDD016*	270,848	7,130,383	565	DDH	-60	110	222	84	99.8	15.8	1.5	15.8m @ 1.5g/t Au from 84m
including								86.9	91.8	5	4.4	5m @ 4.4g/t Au from 86.9m
including								86.9	88.9	2.1	8.4	2.1m @ 8.4g/t Au from 86.9m
HWDD018*	270,834	7,130,152	567	DDH	-60	40	219	108	119	11	1.2	11m @ 1.2g/t Au from 108m
and								137	148	11	0.7	11m @ 0.7g/t Au from 137m
HWDD019*	270,904	7,130,313	567	DDH	-60	40	356.8	29.4	33.1	3.8	1.3	3.8m @ 1.3g/t Au from 29.4m
and								38.4	39.4	1	1.2	1m @ 1.2g/t Au from 38.4m
and								49.2	50	0.8	1.1	0.8m @ 1.1g/t Au from 49.2m
and								58.7	71	12.3	1.0	12.3m @ 1g/t Au from 58.7m
including								58.7	61	2.3	3.4	2.3m @ 3.4g/t Au from 58.7m
and								142.1	143.3	1.2	1.1	1.2m @ 1.1g/t Au from 142.1m
HWDD038	270,830	7,130,143	565	DDH	-60	30	220	66.5	69.9	3.4	1.2	3.4m @ 1.2g/t Au from 66.5m
and								114	176.3	62.3	0.9	62.3m @ 0.9g/t Au from 114m^
including								115.4	121.5	6.1	2.0	6.1m @ 2g/t Au from 115.4m
including								170.7	173.8	3.1	3.0	3.1m @ 3g/t Au from 170.7m
and								192	193	1	0.6	1m @ 0.6g/t Au from 192m
and								195	196	1	0.5	1m @ 0.5g/t Au from 195m
and								204.9	207	2.1	0.5	2.1m @ 0.5g/t Au from 204.9m
HWDD040	270,825	7,130,177	565	DDH	-60	30	180	81	101.2	20.2	1.1	20.2m @ 1.1g/t Au from 81m
including								82.2	85	2.8	3.5	2.8m @ 3.5g/t Au from 82.2m
and								114.4	119.5	5.1	2.9	5.1m @ 2.9g/t Au from 114.4m
and								131	139	8	1.7	8m @ 1.7g/t Au from 131m
including								138	139	1	7.3	1m @ 7.3g/t Au from 138m
and								159	160.5	1.5	0.5	1.5m @ 0.5g/t Au from 159m



For personal use only

Hole ID	Coordinates (MGA94 Zone 51)			Hole Details				Intercept Details				
	Easting (m)	Northing (m)	RL (m)	Hole Type	Azi (deg)	Dip (deg)	Total Depth (m)	Depth from (m)	Depth To (m)	Intercept Width (m)	Grade (g/t)	Grade Summary/ Comments
and								161.5	162	0.5	0.6	0.5m @ 0.6g/t Au from 161.5m
and								164.4	165	0.6	0.6	0.6m @ 0.6g/t Au from 164.4m
HWDD041								47	47.6	0.6	1.3	0.6m @ 1.3g/t Au from 47m
and								75.7	76.4	0.7	1.6	0.7m @ 1.6g/t Au from 75.7m
and								81	99.5	18.5	1.7	18.5m @ 1.7g/t Au from 81m
including								87.6	90.8	3.2	8.0	3.2m @ 8g/t Au from 87.6m
and	270,845	7,130,167	565	DDH	-60	30	215.35	106.3	106.8	0.5	0.5	0.5m @ 0.5g/t Au from 106.3m
and								113.7	114.2	0.5	1.2	0.5m @ 1.2g/t Au from 113.7m
and								119.3	123.3	4	0.9	4m @ 0.9g/t Au from 119.3m
and								132.1	141	8.9	0.9	8.9m @ 0.9g/t Au from 132.1m
and								163	163.5	0.5	0.8	0.5m @ 0.8g/t Au from 163m
HWDD044								39.9	43.1	3.2	1.2	3.2m @ 1.2g/t Au from 39.9m
and	270,828	7,130,181	565	DDH	-65	15	198.14	136.1	148.2	12.1	1.0	12.1m @ 1g/t Au from 136.1m
and								169.8	173	3.2	0.6	3.2m @ 0.6g/t Au from 169.8m
HWDD045								76.4	77.3	0.9	1.1	0.9m @ 1.1g/t Au from 76.4m
and								135	136.5	1.5	0.9	1.5m @ 0.9g/t Au from 135m
and								141	143	2	1.2	2m @ 1.2g/t Au from 141m
and	270,789	7,130,188	565	DDH	-60	30	209.84	147	148.5	1.5	1.4	1.5m @ 1.4g/t Au from 147m
and								153.4	154	0.6	2.3	0.6m @ 2.3g/t Au from 153.4m
and								160	160.9	0.9	1.2	0.9m @ 1.2g/t Au from 160m
AHWR076*								19	26	7	1.7	7m @ 1.7g/t Au from 19m
and	270,879	7,130,232	541	RC	342	-58	72	38	55	17	1.0	17m @ 1g/t Au from 38m
AHWR077*								20	21	1	0.5	1m @ 0.5g/t Au from 20m
and								32	33	1	0.5	1m @ 0.5g/t Au from 32m
and	270,860	7,130,226	541	RC	344	-59	120	39	51	12	2.1	12m @ 2.1g/t Au from 39m
and								64	72	8	2.0	8m @ 2g/t Au from 64m
AHWR078*								36	38	2	0.5	2m @ 0.5g/t Au from 36m
and								57	59	2	0.5	2m @ 0.5g/t Au from 57m
and	270,846	7,130,217	541	RC	342	-60	118	63	88	25	0.8	25m @ 0.8g/t Au from 63m, incl. 6m @ 1.2g/t Au
including								82	88	6	1.2	
and								98	118	20	1.5	20m @ 1.5g/t Au from 98m to BOH
AHWR079*								32	33	1	1.3	1m @ 1.3g/t Au from 32m
and								50	51	1	0.9	1m @ 0.9g/t Au from 50m
and	270,827	7,130,209	541	RC	346	-59	187	56	57	1	0.5	1m @ 0.5g/t Au from 56m
and								69	74	5	1.1	5m @ 1.1g/t Au from 69m



For personal use only

Hole ID	Coordinates (MGA94 Zone 51)			Hole Details				Intercept Details				
	Easting (m)	Northing (m)	RL (m)	Hole Type	Azi (deg)	Dip (deg)	Total Depth (m)	Depth from (m)	Depth To (m)	Intercept Width (m)	Grade (g/t)	Grade Summary/ Comments
and								96	140	44	0.6	44m @ 0.6g/t Au from 96m^, incl. 4m @ 2.6g/t Au
including								134	138	4	2.6	
AHWR080*	270,907	7,130,128	541	RC	74	-64	103	16	18	2	1.0	2m @ 1g/t Au from 16m
and								33	34	1	3.1	1m @ 3g/t Au from 33m
and								44	53	9	1.2	9m @ 1.2g/t Au from 44m
AHWR081*	270,886	7,130,120	541	RC	67	-63	103	33	34	1	4.5	1m @ 4.5g/t Au from 33m
and								45	46	1	1.1	1m @ 1.1g/t Au from 45m
and								72	75	3	0.8	3m @ 0.8g/t Au from 72m
and								82	83	1	1.3	1m @ 1.3g/t Au from 82m
AHWR082*	270,887	7,130,177	541	RC	345	-60	91	4	6	2	1.2	2m @ 1.2g/t Au from 4m
and								13	21	8	1.5	8m @ 1.5g/t Au from 13m, incl. 2m @ 4.4g/t Au
including								16	18	2	4.4	
and								68	69	1	0.6	1m @ 0.6g/t Au from 68m
AHWR083*	270,863	7,130,167	541	RC	72	-60	115	27	28	1	1.0	1m @ 1g/t Au from 27m
and								39	41	2	1.8	2m @ 1.8g/t Au from 39m
AHWR084*	270,845	7,130,155	541	RC	72	-61	151	46	81	35	0.5	35m @ 0.5g/t Au from 46m
AHWR085*	270,903	7,130,283	541	RC	346	-61	73	65	71	6	1.1	6m @ 1.1g/t Au from 65m
AHWR086*	270,849	7,130,276	541	RC	344	-59	97	19	20	1	0.6	1m @ 0.6g/t Au from 19m
and								22	23	1	0.5	1m @ 0.5g/t Au from 22m
and								48	49	1	3.1	1m @ 3.1g/t Au from 48m
AHWR087*	270,832	7,130,264	541	RC	347	-60	92	19	24	5	0.8	5m @ 0.8g/t Au from 19m, incl. 2m @ 1.6g/t Au from 19m
including								19	21	2	1.6	
and								35	36	1	3.6	1m @ 3.6g/t Au from 35m
and								42	43	1	1.3	1m @ 1.3g/t Au from 42m
AHWR088*	270,812	7,130,253	541	RC	349	-59	67	64	65	1	0.5	1m @ 0.5g/t Au from 64m
AHWR089*	270,904	7,130,344	541	RC	270	-60	79	43	46	3	1.9	3m @ 1.9g/t Au from 43m
and								60	61	1	28.6	1m @ 28.6g/t Au from 60m
AHWR090*	270,863	7,130,329	541	RC	90	-60	139	42	48	6	0.5	6m @ 0.5g/t Au from 42m
and								72	84	12	0.7	12m @ 0.7g/t Au from 72m
and								94	95	1	0.9	1m @ 0.9g/t Au from 94m
AHWR091*	270,832	7,130,320	541	RC	270	-60	139	92	120	28	0.7	28m @ 0.7g/t Au from 92m
HWAC1447*	270,700	7,130,500	541	AC	90	-60	51					NSR
HWAC1448*	270,750	7,130,500	541	AC	90	-60	61					NSR
HWAC1449*	270,800	7,130,500	541	AC	71	-58	56					NSR
HWAC1450*	270,850	7,130,500	541	AC	71	-59	57	37	38	1	0.5	1m @ 0.5g/t Au from 37m
HWAC1451*	270,900	7,130,500	541	AC	343	-61	58	31	32	1	1.7	1m @ 1.7g/t Au from 31m
HWAC1452*	270,950	7,130,500	541	AC	341	-60	64	44	45	1	1.2	1m @ 1.2g/t Au from 44m
and								57	60	3	0.5	3m @ 0.5g/t Au from 57m
HWAC1453*	271,000	7,130,500	541	AC	324	-61	61	29	30	1	0.6	1m @ 0.6g/t Au from 29m
HWAC1454*	271,050	7,130,500	541	AC	342	-59	90	48	49	1	0.7	1m @ 0.7g/t Au from 48m
HWAC1482*	270,750	7,130,400	541	AC	90	-60	65					NSR



For personal use only

Hole ID	Coordinates (MGA94 Zone 51)			Hole Details				Intercept Details				
	Easting (m)	Northing (m)	RL (m)	Hole Type	Azi (deg)	Dip (deg)	Total Depth (m)	Depth from (m)	Depth To (m)	Intercept Width (m)	Grade (g/t)	Grade Summary/ Comments
HWAC1483*	270,700	7,130,400	541	AC	75	-60	65					NSR
HWAC1484*	270,800	7,130,400	541	AC	270	-60	69					NSR
HWAC1485*	270,850	7,130,400	541	AC	270	-60	75	32	33	1	0.8	1m @ 0.8g/t Au from 32m
HWAC1486*	270,900	7,130,400	541	AC	270	-60	86					NSR
HWAC1487*	270,950	7,130,400	541	AC	270	-60	71					NSR
HWAC1488*	271,000	7,130,400	541	AC	270	-60	75	1	6	5	1.4	5m @ 1.4g/t Au from 1m
and								11	12	1	0.7	1m @ 0.7g/t Au from 11m
and								17	75	58	1.7	58m @ 1.7g/t Au from 17m to BOH, incl. 10m @ 4.2g/t Au
including								60	70	10	4.2	
HWAC1489*	271,050	7,130,400	541	AC	270	-60	78					NSR
HWAC1519*	270,750	7,130,200	541	AC	345	-60	87					NSR
HWAC1520*	270,800	7,130,200	541	AC	340	-60	93					NSR
HWAC1521*	270,850	7,130,200	541	AC	345	-59	93	8	9	1	0.5	1m @ 0.5g/t Au from 8m
and								18	19	1	0.8	1m @ 0.8g/t Au from 18m
and								43	44	1	1.1	1m @ 1.1g/t Au from 43m
HWAC1522*	270,900	7,130,200	541	AC	343	-58	99	11	12	1	0.5	1m @ 0.5g/t Au from 11m
and								24	26	2	0.7	2m @ 0.7g/t Au from 24m
HWAC1523*	270,950	7,130,200	541	AC	270	-60	100	28	36	8	1.0	8m @ 1g/t Au from 28m
and								41	42	1	1.1	1m @ 1.1g/t Au from 41m
and								80	81	1	0.8	1m @ 0.8g/t Au from 80m
and								90	91	1	0.8	1m @ 0.8g/t Au from 90m
HWAC1524*	271,000	7,130,200	541	AC	270	-60	95	9	10	1	1.5	1m @ 1.5g/t Au from 9m
and								26	29	3	4.3	3m @ 4.3g/t Au from 26m
HWAC1525*	271,050	7,130,200	541	AC	270	-60	89					NSR
HWAC1643*	270,900	7,130,450	541	AC	270	-60	66	30	34	4	0.6	4m @ 0.6g/t Au from 30m
HWAC1643R*	270,900	7,130,450	541	AC	270	-60	75	27	28	1	0.6	1m @ 0.6g/t Au from 27m
and								48	49	1	1.0	1m @ 1g/t Au from 48m
and								70	71	1	0.5	1m @ 0.5g/t Au from 70m
HWAC1644*	270,950	7,130,450	541	AC	270	-60	85					NSR
HWAC1644R*	270,950	7,130,450	541	AC	270	-60	68					NSR
HWAC1645*	271,000	7,130,450	541	AC	270	-60	80					NSR
HWAC1645R*	271,000	7,130,450	541	AC	270	-60	69					NSR
HWAC1646*	271,050	7,130,450	541	AC	270	-60	92	24	25	1	0.6	1m @ 0.6g/t Au from 24m
HWAC1648*	271,050	7,130,350	541	AC	270	-60	95					NSR
HWAC1649*	271,000	7,130,350	541	AC	270	-60	93	44	49	5	0.7	5m @ 0.7g/t Au from 44m, incl. 1m @ 2g/t Au
including								44	45	1	2.0	
and								64	67	3	0.5	3m @ 0.5g/t Au from 64m
HWAC1650*	270,950	7,130,350	541	AC	270	-60	86					NSR
HWAC1651*	271,050	7,130,300	541	AC	270	-60	96					NSR
HWAC1652*	271,000	7,130,300	541	AC	270	-60	102	40	41	1	0.6	1m @ 0.6g/t Au from 40m
and								51	54	3	0.8	3m @ 0.8g/t Au from 51m



For personal use only

Hole ID	Coordinates (MGA94 Zone 51)			Hole Details				Intercept Details				
	Easting (m)	Northing (m)	RL (m)	Hole Type	Azi (deg)	Dip (deg)	Total Depth (m)	Depth from (m)	Depth To (m)	Intercept Width (m)	Grade (g/t)	Grade Summary/ Comments
HWAC1653*	270,950	7,130,300	541	AC	90	-60	106	19	28	9	0.6	9m @ 0.6g/t Au from 19m
HWAC1656*	271,050	7,130,250	541	AC	341	-60	98					NSR
HWAC1657*	271,000	7,130,250	541	AC	342	-60	105					NSR
HWAC1661*	271,050	7,130,150	541	AC	342	-59	96					NSR
HWAC1683*	271,050	7,130,000	541	AC	342	-60	66					NSR
HWAC1684*	271,000	7,130,000	541	AC	340	-60	88					NSR
HWAC1685*	270,950	7,130,000	541	AC	74	-61	94					NSR
HWAC1686*	270,900	7,130,000	541	AC	72	-61	89					NSR
HWAC1687*	270,850	7,130,000	541	AC	78	-64	83					NSR
HWRC072*	270,853	7,130,219	541	RC	349	-59	107	18	107	89	3.0	89m @ 3.0g/t Au from 18m to BOH^, incl. 15m @ 14.2g/t Au
including								18	33	15	14.2	
HWRC073*	270,812	7,130,204	541	RC	350	-60	105	85	105	20	0.8	20m @ 0.8g/t Au from 85m to BOH
HWRC074*	270,949	7,130,248	541	RC	350	-60	113	73	74	1	0.6	1m @ 0.6g/t Au from 73m
and								88	113	25	1.3	25m @ 1.3g/t Au from 88m to BOH, incl. 4m @ 3.8g/t Au
including								100	104	4	3.8	
HWRC075*	270,745	7,130,394	541	RC	75	-61	107					NSR
HWRC076*	270,793	7,130,408	541	RC	90	-60	95					NSR
HWRC091*	270,901	7,130,230	541	RC	345	-60	110	6	32	26	2.0	26m @ 2.0g/t Au from 6m
and								76	77	1	0.6	1m @ 0.6g/t Au from 76m
HWRC092*	270,907	7,130,211	541	RC	344	-59	117	12	33	21	0.8	21m @ 0.8g/t Au from 12m, incl. 4m @ 1.6g/t Au from 28m
including								28	32	4	1.6	
and								41	66	25	0.9	25m @ 0.9g/t Au from 41m, incl. 8m @ 1.7g/t Au from 50m
including								50	58	8	1.7	
HWRC093*	270,916	7,130,188	541	RC	345	-60	117	74	100	26	1.8	26m @ 1.8g/t Au from 74m
HWRC094*	270,875	7,130,226	541	RC	345	-60	111	15	16	1	1.0	1m @ 1g/t Au from 15m
and								20	32	12	0.7	12m @ 0.7g/t Au from 20m
and								47	58	11	0.7	11m @ 0.7g/t Au from 47m
HWRC095*	270,889	7,130,202	541	RC	343	-61	117	25	34	9	0.5	9m @ 0.5g/t Au from 25m
and								42	50	8	0.7	8m @ 0.7g/t Au from 42m
and								64	66	2	4.4	2m @ 4.4g/t Au from 64m
and								78	79	1	0.5	1m @ 0.5g/t Au from 78m
and								87	91	4	3.4	4m @ 3.4g/t Au from 87m
and								103	106	3	0.6	3m @ 0.6g/t Au from 103m
and												
HWRC096*	270,894	7,130,179	541	RC	345	-60	117	5	14	9	1.5	9m @ 1.5g/t Au from 5m
and								65	97	32	1.2	32m @ 1.2g/t Au from 65m, incl. 7m @ 3.2g/t Au from 68m
including								68	75	7	3.2	
and								112	117	5	1.0	5m @ 1g/t Au from 112m to BOH
HWRC097*	270,853	7,130,219	541	RC	342	-60	117	50	51	1	4.2	1m @ 4.2g/t Au from 50m
and								58	59	1	0.5	1m @ 0.5g/t Au from 58m
HWRC098*	270,862	7,130,191	541	RC	342	-59	117	35	36	1	0.6	1m @ 0.6g/t Au from 35m
and								41	48	7	0.5	7m @ 0.5g/t Au from 41m



For personal use only

Hole ID	Coordinates (MGA94 Zone 51)			Hole Details				Intercept Details				
	Easting (m)	Northing (m)	RL (m)	Hole Type	Azi (deg)	Dip (deg)	Total Depth (m)	Depth from (m)	Depth To (m)	Intercept Width (m)	Grade (g/t)	Grade Summary/ Comments
and								53	56	3	0.5	3m @ 0.5g/t Au from 53m
and								108	111	3	0.5	3m @ 0.5g/t Au from 108m
and								115	117	2	1.8	2m @ 1.8g/t Au from 115m to BOH
HWRC099*								41	43	2	1.4	2m @ 1.4g/t Au from 41m
and	270,869	7,130,170	541	RC	67	-62	117	72	98	26	0.5	26m @ 0.5g/t Au from 72m
and								112	117	5	2.0	5m @ 2g/t Au from 112m to BOH
HWRC100*	270,832	7,130,213	541	RC	343	-60	117	89	94	5	0.5	5m @ 0.5g/t Au from 89m
and								101	106	5	0.8	5m @ 0.8g/t Au from 101m
HWRC101*	270,837	7,130,186	541	RC	344	-60	111					NSR
HWRC102*	270,844	7,130,163	541	RC	71	-63	117	96	97	1	0.8	1m @ 0.8g/t Au from 96m
HWRC103*								22	28	6	0.8	6m @ 0.8g/t Au from 22m
and								54	56	2	0.6	2m @ 0.6g/t Au from 54m
and								69	70	1	0.6	1m @ 0.6g/t Au from 69m
and	270,877	7,130,307	541	RC	90	-60	108	78	82	4	1.5	4m @ 1.5g/t Au from 78m
and								93	94	1	0.5	1m @ 0.5g/t Au from 93m
and								97	98	1	0.6	1m @ 0.6g/t Au from 97m
and								105	106	1	0.6	1m @ 0.6g/t Au from 105m
HWRC104*								25	26	1	1.0	1m @ 1g/t Au from 25m
and	270,887	7,130,284	541	RC	344	-60	117	100	102	2	0.5	2m @ 0.5g/t Au from 100m
and								105	114	9	0.5	9m @ 0.5g/t Au from 105m
and								116	117	1	0.5	1m @ 0.5g/t Au from 116m
HWRC105*								16	17	1	0.9	1m @ 0.9g/t Au from 16m
and								36	37	1	0.5	1m @ 0.5g/t Au from 36m
and	270,893	7,130,256	541	RC	26	-60	117	49	50	1	1.8	1m @ 1.8g/t Au from 49m
and								100	101	1	0.5	1m @ 0.5g/t Au from 100m
and								104	105	1	0.5	1m @ 0.5g/t Au from 104m
HWRC112*								16	18	2	1.2	2m @ 1.2g/t Au from 16m
and	270,922	7,130,163	541	RC	72	-61	123	42	48	6	1.4	6m @ 1.4g/t Au from 42m
and								103	123	20	0.8	20m @ 0.8g/t Au from 103m to BOH
HWRC113*	270,922	7,130,238	541	RC	211	-60	94					NSR
HWRC114*	270,954	7,130,093	541	RC	73	-60	117					NSR
HWRC115*								0	1	1	0.7	1m @ 0.7g/t Au from 0m
and								19	20	1	0.7	1m @ 0.7g/t Au from 19m
and	270,940	7,130,113	541	RC	73	-60	117	27	28	1	1.2	1m @ 1.2g/t Au from 27m
and								45	47	2	0.5	2m @ 0.5g/t Au from 45m
and								53	59	6	0.5	6m @ 0.5g/t Au from 53m
HWRC116*	270,929	7,130,145	541	RC	73	-60	94	10	49	39	0.7	39m @ 0.7g/t Au from 10m
and								89	90	1	0.8	1m @ 0.8g/t Au from 89m
HWRC117*	270,951	7,130,166	541	RC	69	-61	117					NSR
HWRC118*	270,942	7,130,191	541	RC	342	-60	117	14	15	1	0.6	1m @ 0.6g/t Au from 14m





For personal use only

Hole ID	Coordinates (MGA94 Zone 51)			Hole Details				Intercept Details				
	Easting (m)	Northing (m)	RL (m)	Hole Type	Azi (deg)	Dip (deg)	Total Depth (m)	Depth from (m)	Depth To (m)	Intercept Width (m)	Grade (g/t)	Grade Summary/ Comments
and								20	22	2	0.6	2m @ 0.6g/t Au from 20m
and								35	36	1	1.7	1m @ 1.7g/t Au from 35m
HWRC119*	270,930	7,130,218	541	RC	342	-60	117	18	19	1	1.1	1m @ 1.1g/t Au from 18m
and								26	27	1	0.6	1m @ 0.6g/t Au from 26m
and								30	32	2	0.6	2m @ 0.6g/t Au from 30m
HWRC120*	270,833	7,130,291	541	RC	20	-60	117					NSR
HWRC121*	270,839	7,130,269	541	RC	20	-60	117	20	25	5	1.2	5m @ 1.2g/t Au from 20m
and								42	50	8	2.5	8m @ 2.5g/t Au from 42m, incl. 2m @ 8g/t Au from 42m
including								42	44	2	8.0	
and								62	64	2	0.5	2m @ 0.5g/t Au from 62m
HWRC122*	270,844	7,130,245	541	RC	20	-60	117	38	40	2	1.9	2m @ 1.9g/t Au from 38m
and								48	63	15	0.6	15m @ 0.6g/t Au from 48m
and								91	95	4	1.0	4m @ 1g/t Au from 91m
HWRC123*	270,920	7,130,342	541	RC	90	-60	117	61	63	2	1.4	2m @ 1.4g/t Au from 61m
HWRC124*	270,917	7,130,342	541	RC	90	-60	117	10	11	1	1.0	1m @ 1g/t Au from 10m
and								15	49	34	0.6	34m @ 0.6g/t Au from 15m
and								60	65	5	0.7	5m @ 0.74g/t Au from 60m
and								84	89	5	1.4	5m @ 1.4g/t Au from 84m
HWRC125*	270,934	7,130,296	541	RC	90	-60	117	10	19	9	1.2	9m @ 1.2g/t Au from 10m
and								33	41	8	3.2	8m @ 3.2g/t Au from 33m
and								50	109	59	0.8	59m @ 0.8g/t Au from 50m^
HWRC126*	270,940	7,130,272	541	RC	20	-60	117	66	67	1	0.9	1m @ 0.9g/t Au from 66m
HWRC127*	270,964	7,130,360	541	RC	90	-60	117	83	113	30	1.7	30m @ 1.7g/t Au from 83m
HWRC128*	270,975	7,130,335	541	RC	90	-60	117	19	20	1	0.6	1m @ 0.6g/t Au from 19m
and								111	112	1	0.6	1m @ 0.6g/t Au from 111m
and								115	116	1	0.5	1m @ 0.5g/t Au from 115m
HWRC129*	270,986	7,130,309	541	RC	90	-60	124	80	81	1	0.5	1m @ 0.5g/t Au from 80m
HWRC130*	270,990	7,130,290	541	RC	90	-60	117	59	61	2	1.3	2m @ 1.3g/t Au from 59m
HWRC131*	271,016	7,130,372	541	RC	90	-60	117	35	43	8	1.2	8m @ 1.2g/t Au from 35m
HWRC132*	271,026	7,130,351	541	RC	90	-60	117	61	65	4	0.6	4m @ 0.6g/t Au from 61m
and								75	78	3	0.5	3m @ 0.5g/t Au from 75m
and								109	112	3	0.6	3m @ 0.6g/t Au from 109m
HWRC133*	271,032	7,130,328	541	RC	90	-60	117					NSR
HWRC167*	270,875	7,130,172	541	RC	20	-60	83	16	17	1	3.2	1m @ 3.2g/t Au from 16m
and								66	69	3	0.5	3m @ 0.5g/t Au from 66m
and								76	79	3	3.0	3m @ 3g/t Au from 76m
HWRC168*	270,863	7,130,273	541	RC	20	-60	53	42	45	3	0.5	3m @ 0.5g/t Au from 42m
and								49	50	1	0.6	1m @ 0.6g/t Au from 49m
HWRC221*	270,875	7,130,147	541	RC	69	-61	221					NSR
HWRC222*	270,936	7,130,129	541	RC	71	-60	155	9	43	34	0.8	34m @ 0.8g/t Au from 9m^
HWRC223*	270,983	7,130,184	541	RC	343	-59	125					NSR



Hole ID	Coordinates (MGA94 Zone 51)			Hole Details				Intercept Details				
	Easting (m)	Northing (m)	RL (m)	Hole Type	Azi (deg)	Dip (deg)	Total Depth (m)	Depth from (m)	Depth To (m)	Intercept Width (m)	Grade (g/t)	Grade Summary/ Comments
HWRC224*	270,969	7,130,131	541	RC	270	-60	149					NSR
HWRC225*	270,790	7,130,285	541	RC	20	-60	113	85	86	1	2.4	1m @ 2.4g/t Au from 85m
HWRC226*	270,763	7,130,231	541	RC	20	-60	131	104	106	2	0.5	2m @ 0.5g/t Au from 104m
and								111	115	4	0.6	4m @ 0.6g/t Au from 111m
HWRC227*	270,745	7,130,184	541	RC	20	-60	125					NSR
HWRC228*	270,953	7,130,099	541	RC	270	-60	143	8	24	16	0.5	16m @ 0.5g/t Au from 8m
HWRC234*	270,841	7,130,423	541	RC	90	-60	209	31	32	1	0.8	1m @ 0.8g/t Au from 31m
and								38	39	1	1.0	1m @ 1g/t Au from 38m
and								119	120	1	0.5	1m @ 0.5g/t Au from 119m
HWRC235*	270,728	7,130,389	541	RC	252	-60	203					NSR
HWRC236*	270,786	7,130,193	541	RC	73	-60	299	110	179	69	0.7	69m @ 0.7g/t Au from 110m^, incl. 4m @ 2.6g/t Au
including								173	177	4	2.6	
HWRC237*	270,857	7,130,113	541	RC	270	-60	280	67	73	6	0.6	6m @ 0.6g/t Au from 67m
and								83	84	1	0.5	1m @ 0.5g/t Au from 83m
and								105	107	2	0.5	2m @ 0.5g/t Au from 105m
and								110	111	1	0.5	1m @ 0.5g/t Au from 110m
HWRC251*	270,720	7,130,172	541	RC	72	-60	280	144	239	95	0.7	95m @ 0.7g/t Au from 144m^, incl. 10m @ 3.5g/t Au
including								229	239	10	3.5	
and								258	264	6	0.6	

\*Previously announced or historic result

^Reported bulk intercept includes internal waste: AHWR079 (13m), HWRC072 (13m), HWRC125 (11m), HWRC222 (10m), HWRC236 (16m), HWRC251 (17m), HWDD038 (18m).

A cutoff of 0.3g/t Au was applied to each significant intercept.

For personal use only



**Table 3 – Warmblood**

Hole ID	Coordinates (MGA94 Zone 51)			Hole Details				Intercept Details				
	Easting (m)	Northing (m)	RL (m)	Hole Type	Azi (deg)	Dip (deg)	Total Depth (m)	Depth from (m)	Depth To (m)	Intercept Width (m)	Grade (g/t)	Grade Summary/ Comments
HWDD017*	271,830	7,128,780	569	RC_DD	72.5	-60	186	114	128.4	14.4	6.0	14.4m @ 6.0g/t Au from 114m
including								115	122	7	10.6	7m @ 10.6g/t Au from 115m
and								144	156.7	12.7	1.7	12.7m @ 1.7g/t Au from 144m
HWDD028*	271,917	7,128,493	569	DDH	-68	72.5	139.4	74.7	77	2.3	0.5	2.3m @ 0.5g/t Au from 74.7m
HWDD029*	271,902	7,128,568	569	DDH	-68	72.5	109.6	8.6	24	15.4	0.8	15.4m @ 0.8g/t Au from 8.6m
and								27	46	19	0.3	19m @ 0.3g/t Au from 27m
and								49.6	57	7.4	5.0	7.4m @ 5g/t Au from 49.6m
including								49.6	52.6	3	10.6	3m @ 10.6g/t Au from 49.6m
and								64	65	1	1.2	1m @ 1.2g/t Au from 64m
HWDD039*	271,854	7,128,746	569	DDH	-60	72.5	155.9	28.6	30.4	1.8	1.6	1.8m @ 1.6g/t Au from 28.6m
and								102.5	117	14.6	1.5	14.6m @ 1.5g/t Au from 102.5m
including								102.5	105.8	3.3	4.2	3.3m @ 4.2g/t Au from 102.5m
and								127.2	140	12.8	1.6	12.8m @ 1.6g/t Au from 127.2m
HWDD042*	271,792	7,128,852	569	DDH	-60	72.5	222.4	117	121.1	4.1	0.4	4.1m @ 0.4g/t Au from 117m
and								129.6	131	1.4	0.4	1.4m @ 0.4g/t Au from 129.6m
and								138.5	146.4	7.9	9.7	7.9m @ 9.7g/t Au from 138.5m
including								141.8	145	3.2	22.0	3.2m @ 22g/t Au from 141.8m
and								169.8	179.6	9.9	0.6	9.9m @ 0.6g/t Au from 169.8m
HWDD043*	271,745	7,128,920	569	DDH	-60	72.5	245.6	171.7	176.9	5.2	3.1	5.2m @ 3.1g/t Au from 171.7m
including								174.7	176.9	3.2	7.0	3.2m @ 7g/t Au from 174.7m
and								203.6	211	7.4	1.1	7.4m @ 1.1g/t Au from 203.6m
and								211.5	215	3.5	0.4	3.5m @ 0.4g/t Au from 211.5m
HWRC263*	271,906	7,128,805	569	RC	72.5	-60	94	39	44	5	0.4	5m @ 0.4g/t Au from 39m
HWRC264*	271,868	7,128,792	569	RC	72.5	-60	154	32	36	4	0.4	4m @ 0.4g/t Au from 32m
and								70	76	6	1.5	6m @ 1.5g/t Au from 70m
including								72	74	2	3.6	2m @ 3.6g/t Au from 72m
and								94	103	9	2.6	9m @ 2.6g/t Au from 94m
including								95	99	4	4.9	4m @ 4.9g/t Au from 95m
HWRC265*	271,885	7,128,840	569	RC	72.5	-60	124	53	56	3	3.5	3m @ 3.5g/t Au from 53m
HWRC266*	271,855	7,128,704	569	RC	72.5	-60	154	109	110	1	3.2	1m @ 3.2g/t Au from 109m
and								112	114	2	0.7	2m @ 0.7g/t Au from 112m
and								128	130	2	0.5	2m @ 0.5g/t Au from 128m
HWRC275*	271,912	7,128,722	569	RC	72.5	-60	124	4	5	1	0.4	1m @ 0.4g/t Au from 4m
and								37	43	6	4.0	6m @ 4g/t Au from 37m
including								38	41	3	7.6	3m @ 7.6g/t Au from 38m
and								62	69	7	1.1	7m @ 1.1g/t Au from 62m

For personal use only



Hole ID	Coordinates (MGA94 Zone 51)			Hole Details				Intercept Details				
	Easting (m)	Northing (m)	RL (m)	Hole Type	Azi (deg)	Dip (deg)	Total Depth (m)	Depth from (m)	Depth To (m)	Intercept Width (m)	Grade (g/t)	Grade Summary/ Comments
HWRC329*	271,817	7,128,902	569	RC	-60	72.5	150	102	108	6	2.5	6m @ 2.5g/t Au from 102m
including								106	108	2	5.0	2m @ 5g/t Au from 106m
HWRC330*	271,830	7,128,864	569	RC	-60	72.5	162	24	25	1	0.7	1m @ 0.7g/t Au from 24m
and								42	44	2	1.1	2m @ 1.1g/t Au from 42m
and								114	119	5	2.0	5m @ 2g/t Au from 114m
HWRC331*	271,847	7,128,827	569	RC	-60	72.5	162	23	24	1	0.3	1m @ 0.3g/t Au from 23m
and								87	88	1	0.9	1m @ 0.9g/t Au from 87m
and								101	102	1	0.4	1m @ 0.4g/t Au from 101m
HWRC332*	271,931	7,128,771	569	RC	-60	72.5	114					NSR
HWRC333*	271,893	7,128,758	569	RC	-60	72.5	126	21	22	1	1.0	1m @ 1g/t Au from 21m
and								51	54	3	0.6	3m @ 0.6g/t Au from 51m
and								69	70	1	1.1	1m @ 1.1g/t Au from 69m
HWRC334*	271,931	7,128,729	569	RC	-60	72.5	66	35	41	6	1.0	6m @ 1g/t Au from 35m
HWRC335*	271,919	7,128,683	569	RC	-60	72.5	114	16	30	14	0.3	14m @ 0.3g/t Au from 16m
HWRC349	271,779	7,128,934	569	RC	-60	72.5	192	94	96	2	1.5	2m @ 1.5g/t Au from 94m
and								100	101	1	0.7	1m @ 0.7g/t Au from 100m
and								150	155	5	1.9	5m @ 1.9g/t Au from 150m
HWRC350	271,754	7,128,975	569	RC	-60	72.5	175					NSR
HWRC351	271,714	7,129,075	569	RC	-60	72.5	175	125	127	2	1.0	2m @ 1g/t Au from 125m
HWRC352	271,711	7,129,018	569	RC	-60	72.5	175	126	127	1	1.5	1m @ 1.5g/t Au from 126m
HWRC353	271,575	7,129,298	569	RC	-60	72.50	174	80	84	4	0.5	4m @ 0.5g/t Au from 80m
and								140	141	1	0.7	1m @ 0.7g/t Au from 140m
and								144	145	1	0.5	1m @ 0.5g/t Au from 144m
HWRC355	271,544	7,129,383	569	RC	-60	72.5	126					NSR
HWRC356	271,497	7,129,475	569	RC	-60	73	198	0	4	4	1.7	4m @ 1.7g/t Au from 0m
and								86	87	1	0.5	1m @ 0.5g/t Au from 86m
and								90	91	1	0.7	1m @ 0.7g/t Au from 90m
and								110	111	1	0.9	1m @ 0.9g/t Au from 110m
HWRC357	271,497	7,129,359	569	RC	-60	72.5	159					NSR
HWRC358	271,452	7,129,570	569	RC	-60	72.5	181					NSR
AHWA351*	271,925	7,128,543	570	AC	360	-90	45	12	20	8	4.4	8m @ 4.4g/t Au from 12m
AHWA352*	271,933	7,128,542	570	AC	360	-90	46	13	14	1	0.4	1m @ 0.4g/t Au from 13m
and								20	28	8	4.8	8m @ 4.8g/t Au from 20m, incl. 3m @ 11.3g/t Au
including								22	25	3	11.3	
AHWA353*	271,943	7,128,549	570	AC	360	-90	52	0	32	32	3.9	32m @ 3.9g/t Au from 0m, incl 16m @ 6.6g/t Au
including								0	16	16	6.6	
AHWA354*	271,941	7,128,490	571	AC	360	-90	48	12	16	4	0.3	4m @ 0.3g/t Au from 12m
AHWA355*	271,949	7,128,496	571	AC	360	-90	51					NSR
AHWA356*	271,960	7,128,502	571	AC	360	-90	57	0	40	40	3.4	40m @ 3.4g/t Au from 0m, incl. 12m @ 9.0g/t Au
including								28	40	12	9.0	
AHWA357*	271,968	7,128,505	571	AC	360	-90	68	20	28	8	0.6	8m @ 0.6g/t Au from 20m
AHWA358*	271,978	7,128,513	571	AC	360	-90	66	20	24	4	0.3	4m @ 0.3g/t Au from 20m
AHWA394*	271,837	7,128,956	565	AC	70	-60	69					NSR

For personal use only



Hole ID	Coordinates (MGA94 Zone 51)			Hole Details				Intercept Details				
	Easting (m)	Northing (m)	RL (m)	Hole Type	Azi (deg)	Dip (deg)	Total Depth (m)	Depth from (m)	Depth To (m)	Intercept Width (m)	Grade (g/t)	Grade Summary/ Comments
AHWA395*	271,807	7,128,948	567	AC	70	-60	72	48	52	4	1.3	4m @ 1.3g/t Au from 48m
AHWA396*	271,788	7,128,944	567	AC	70	-60	68					NSR
AHWA397*	271,764	7,128,933	571	AC	65	-60	53					NSR
AHWA398*	271,744	7,128,931	573	AC	70	-60	48					NSR
AHWA399*	271,693	7,128,908	573	AC	70	-60	41					NSR
AHWA400*	271,782	7,129,046	568	AC	70	-60	60	25	44	19	1.7	19m @ 1.7g/t Au from 25m
AHWA401*	271,755	7,129,037	569	AC	70	-60	75	34	35	1	0.7	1m @ 0.7g/t Au from 34m
and								60	75	15	4.2	15m @ 4.2g/t Au from 60m
AHWA402*	272,009	7,128,905	568	AC	75	-60	48					NSR
AHWA403*	271,961	7,128,892	567	AC	70	-60	58					NSR
AHWA404*	271,917	7,128,873	570	AC	70	-60	64					NSR
AHWA405*	271,863	7,128,867	567	AC	70	-60	83	68	80	12	1.7	12m @ 1.7g/t Au from 68m
AHWA406*	271,844	7,128,850	567	AC	70	-60	84					NSR
AHWA407*	271,817	7,128,845	565	AC	70	-60	63					NSR
AHWA408*	271,795	7,128,834	567	AC	70	-60	58					NSR
AHWA409*	271,769	7,128,828	570	AC	70	-60	59					NSR
AHWA410*	271,745	7,128,819	571	AC	70	-60	59					NSR
AHWA411*	271,727	7,128,812	571	AC	70	-60	45					NSR
AHWA412*	271,746	7,129,247	566	AC	70	-60	72	36	40	4	1.2	4m @ 1.2g/t Au from 36m
AHWA413*	271,725	7,129,238	565	AC	70	-60	69	44	52	8	22.0	8m @ 22g/t Au from 44m. Incl. 4m @ 43.6g/t Au
including								44	48	4	43.6	
AHWA414*	271,696	7,129,229	567	AC	70	-60	71					NSR
AHWA415*	271,677	7,129,222	567	AC	70	-60	72					NSR
AHWA416*	271,650	7,129,217	569	AC	70	-60	69					NSR
AHWA417*	271,628	7,129,205	569	AC	70	-60	65					NSR
AHWA418*	271,601	7,129,197	566	AC	70	-60	64					NSR
AHWA419*	271,580	7,129,195	565	AC	70	-60	64	44	52	8	0.7	8m @ 0.7g/t Au from 44m
AHWA420*	271,555	7,129,188	567	AC	70	-60	63					NSR
AHWR012*	271,890	7,128,893	569	RC	70	-60	90	32	36	4	0.5	4m @ 0.5g/t Au from 32m
AHWR013*	271,867	7,128,877	569	RC	70	-60	111	56	68	12	0.7	12m @ 0.7g/t Au from 56m
AHWR014*	271,866	7,128,936	569	RC	70	-60	99	24	32	8	0.5	8m @ 0.5g/t Au from 24m
AHWR015*	271,846	7,128,925	569	RC	70	-60	114	40	48	8	0.4	8m @ 0.4g/t Au from 40m
and								56	60	4	0.4	4m @ 0.4g/t Au from 56m
AHWR016*	271,855	7,128,959	569	RC	70	-60	63	28	36	8	0.4	8m @ 0.4g/t Au from 28m
AHWR017*	271,833	7,128,953	569	RC	70	-60	108	48	56	8	1.6	8m @ 1.6g/t Au from 48m
AHWR018*	271,811	7,128,946	569	RC	70	-60	123					NSR
AHWR019*	271,853	7,129,011	569	RC	70	-60	66					NSR
AHWR020*	271,834	7,129,004	569	RC	70	-60	90					NSR
AHWR021*	271,814	7,128,997	569	RC	70	-60	111					NSR
AHWR022*	271,796	7,128,990	569	RC	70	-60	111	52	56	4	0.4	4m @ 0.4g/t Au from 52m
AHWR023*	271,778	7,128,981	569	RC	70	-60	111	52	56	4	0.5	4m @ 0.5g/t Au from 52m
AHWR024*	271,799	7,129,024	569	RC	70	-60	72	28	36	8	1.9	8m @ 1.9g/t Au from 28m
AHWR025*	271,783	7,129,015	569	RC	70	-60	90	20	24	4		4m @ g/t Au from 20m

For Personal Use Only



Hole ID	Coordinates (MGA94 Zone 51)			Hole Details				Intercept Details				
	Easting (m)	Northing (m)	RL (m)	Hole Type	Azi (deg)	Dip (deg)	Total Depth (m)	Depth from (m)	Depth To (m)	Intercept Width (m)	Grade (g/t)	Grade Summary/ Comments
AHWR026*	271,760	7,129,012	569	RC	70	-60	120					NSR
AHWR027*	271,784	7,129,071	569	RC	70	-60	60	16	24	8	2.3	8m @ 2.3g/t Au from 16m
AHWR028*	271,767	7,129,060	569	RC	70	-60	90					NSR
AHWR029*	271,746	7,129,053	569	RC	70	-60	120	68	76	8	0.4	8m @ 0.4g/t Au from 68m
AHWR030*	271,973	7,128,529	571	RC	249	-54	120	13	36	23	0.5	23m @ 0.5g/t Au from 13m
and								40	45	5	0.8	5m @ 0.8g/t Au from 40m
AHWR031*	271,993	7,128,536	572	RC	256	-54	132	20	21	1	0.7	1m @ 0.7g/t Au from 20m
and								37	41	4	0.3	4m @ 0.3g/t Au from 37m
and								48	49	1	0.3	1m @ 0.3g/t Au from 48m
and								70	102	32	1.7	32m @ 1.7g/t Au from 70m, incl. 8m @ 5.5g/t Au
including								93	101	8	5.5	
and								108	109	1	0.5	1m @ 0.5g/t Au from 108m
AHWR032*	271,965	7,128,569	570	RC	250	-54	90	0	7	7	0.4	7m @ 0.4g/t Au from 0m
and								18	43	25	0.6	25m @ 0.6g/t Au from 18m
and								57	62	5	1.1	5m @ 1.1g/t Au from 57m
AHWR033*	271,978	7,128,573	570	RC	250	-55	132	10	12	2	0.3	2m @ 0.3g/t Au from 10m
and								19	61	42	1.1	42m @ 1.1g/t Au from 19m
and								66	68	2	1.0	2m @ 1g/t Au from 66m
and								99	112	13	0.4	13m @ 0.4g/t Au from 99m
AHWR034*	271,989	7,128,492	572	RC	249	-56	108	44	47	3	0.5	3m @ 0.5g/t Au from 44m
and								52	55	3	0.7	3m @ 0.7g/t Au from 52m
and								60	63	3	1.1	3m @ 1.1g/t Au from 60m
and								71	87	16	2.7	16m @ 2.7g/t Au from 71m, incl. 7m @ 4.6g/t Au
including								79	86	7	4.6	
AHWR035*	272,006	7,128,499	572	RC	250	-55	162					NSR
AHWR038*	271,962	7,128,440	571	RC	71	-60	114	12	30	18	2.4	18m @ 2.4g/t Au from 12m, incl. 5m @ 5.1g/t Au
including								14	19	5	5.1	
and								38	40	2	6.3	2m @ 6.3g/t Au from 38m
AHWR039*	271,943	7,128,433	571	RC	70	-59	162	33	34	1	0.3	1m @ 0.3g/t Au from 33m
and								38	45	7	1.0	7m @ 1g/t Au from 38m
and								58	64	6	0.6	6m @ 0.6g/t Au from 58m
AHWR040*	271,976	7,128,402	572	RC	71	-60	156	18	19	1	0.4	1m @ 0.4g/t Au from 18m
and								21	22	1	0.4	1m @ 0.4g/t Au from 21m
and								32	33	1	8.6	1m @ 8.6g/t Au from 32m
and								37	40	3	0.7	3m @ 0.7g/t Au from 37m
AHWR041*	271,955	7,128,395	572	RC	72	-60	126	35	49	14	0.7	14m @ 0.7g/t Au from 35m
AHWR042*	271,983	7,128,362	572	RC	71	-59	156	19	20	1	0.4	1m @ 0.4g/t Au from 19m
and								23	24	1	0.3	1m @ 0.3g/t Au from 23m
AHWR043*	271,923	7,128,549	570	RC	68	-60	39	3	5	2	0.3	2m @ 0.3g/t Au from 3m
and								10	32	22	3.7	22m @ 3.7g/t Au from 10m, incl. 9m @ 5.2g/t Au
including								10	19	9	5.2	
AHWR044*	271,904	7,128,542	570	RC	68	-60	39	14	32	18	0.9	18m @ 0.9g/t Au from 14m, incl. 3m @ 3.7g/t Au
including								14	17	3	3.7	

For personal use only



Hole ID	Coordinates (MGA94 Zone 51)			Hole Details				Intercept Details				
	Easting (m)	Northing (m)	RL (m)	Hole Type	Azi (deg)	Dip (deg)	Total Depth (m)	Depth from (m)	Depth To (m)	Intercept Width (m)	Grade (g/t)	Grade Summary/ Comments
AHWR045*	271,951	7,128,603	569	RC	68	-61	69	12	34	22	0.4	22m @ 0.4g/t Au from 12m
AHWR046*	271,931	7,128,597	569	RC	68	-61	59	19	21	2	0.7	2m @ 0.7g/t Au from 19m
and								24	33	9	0.5	9m @ 0.5g/t Au from 24m
AHWR047*	271,908	7,128,591	570	RC	68	-61	69	14	21	7	1.9	7m @ 1.9g/t Au from 14m, incl. 1m @ 10.9g/t Au
including								15	16	1	10.9	
and								27	36	9	0.3	9m @ 0.3g/t Au from 27m
and								51	56	5	3.2	5m @ 3.2g/t Au from 51m
AHWR048*	271,892	7,128,581	570	RC	68	-65	89	28	39	11	2.3	11m @ 2.3g/t Au from 28m
and								54	80	26	1.8	26m @ 1.8g/t Au from 54m, incl. 6m @ 6.5g/t Au
including								54	60	6	6.5	
AHWR049*	271,969	7,128,695	569	RC	68	-60	69					NSR
AHWR050*	271,933	7,128,683	569	RC	68	-60	69					NSR
AHWR051*	271,892	7,128,666	569	RC	74	-60	69	20	47	27	1.2	27m @ 1.2g/t Au from 20m, incl. 8m @ 3g/t Au
including								35	43	8	3.0	
AHWR052*	271,848	7,128,651	569	RC	68	-60	69					NSR
AHWR053*	271,949	7,128,776	569	RC	68	-60	79					NSR
AHWR054*	271,910	7,128,763	569	RC	68	-60	69					NSR
AHWR055*	271,865	7,128,748	569	RC	68	-60	69	61	63	2	0.4	2m @ 0.4g/t Au from 61m
AHWR056*	271,946	7,128,478	571	RC	73	-60	37	15	20	5	1.1	5m @ 1.1g/t Au from 15m
AHWR057*	271,929	7,128,472	571	RC	71	-60	55	46	49	3	13.6	3m @ 13.6g/t Au from 46m, incl. 1m @ 35.4g/t Au
including								47	48	1	35.4	
and								53	55	2	1.3	2m @ 1.3g/t Au from 53m
AHWR058*	271,920	7,128,638	569	RC	72	-60	48	15	26	11	0.5	11m @ 0.5g/t Au from 15m
AHWR059*	271,904	7,128,630	569	RC	70	-61	68	21	42	21	1.0	21m @ 1g/t Au from 21m
AHWR060*	271,881	7,128,623	569	RC	71	-61	88	30	32	2	0.4	2m @ 0.4g/t Au from 30m
and								39	41	2	0.6	2m @ 0.6g/t Au from 39m
and								65	69	4	1.0	4m @ 1g/t Au from 65m
AHWR061*	271,909	7,128,681	569	RC	72	-61	48	21	24	3	0.6	3m @ 0.6g/t Au from 21m
and								28	30	2	0.8	2m @ 0.8g/t Au from 28m
and								32	43	11	1.1	11m @ 1.1g/t Au from 32m
AHWR062*	271,870	7,128,661	569	RC	74	-61	94	43	49	6	2.3	6m @ 2.3g/t Au from 43m
and								57	58	1	4.1	1m @ 4.1g/t Au from 57m
and								70	81	11	1.2	11m @ 1.2g/t Au from 70m
AHWR063*	271,894	7,128,721	569	RC	75	-61	58	24	26	2	0.9	2m @ 0.9g/t Au from 24m
and								54	58	4	2.9	4m @ 2.9g/t Au from 54m to BOH
AHWR064*	271,872	7,128,713	569	RC	76	-60	78	5	7	2	1.4	2m @ 1.4g/t Au from 5m
and								66	68	2	1.8	2m @ 1.8g/t Au from 66m
AHWR065*	271,853	7,128,709	569	RC	77	-61	99					NSR
AHWR066*	271,880	7,128,755	569	RC	74	-60	59					NSR
AHWR067*	271,845	7,128,657	569	RC	71	-60	152					NSR
AHWR068*	271,855	7,128,623	569	RC	71	-60	143	20	21	1	0.5	1m @ 0.5g/t Au from 20m
and								36	37	1	0.6	1m @ 0.6g/t Au from 36m

For personal use only



Hole ID	Coordinates (MGA94 Zone 51)			Hole Details				Intercept Details				
	Easting (m)	Northing (m)	RL (m)	Hole Type	Azi (deg)	Dip (deg)	Total Depth (m)	Depth from (m)	Depth To (m)	Intercept Width (m)	Grade (g/t)	Grade Summary/ Comments
and								43	46	3	0.6	3m @ 0.6g/t Au from 43m
and								53	75	22	5.6	22m @ 5.6g/t Au from 53m, incl. 4m @ 20.1g/t Au
including								67	71	4	20.1	
and								89	92	3	1.6	3m @ 1.6g/t Au from 89m
AHWR069*	271,859	7,128,576	569	RC	67	-60	160	83	107	24	3.7	24m @ 3.7g/t Au from 83m, incl. 10m @ 7.8g/t Au
including								85	95	10	7.8	
AHWR070*	271,910	7,128,519	570	RC	67	-60	110	69	77	8	2.7	8m @ 2.7g/t Au from 69m
and								82	92	10	1.1	10m @ 1.1g/t Au from 82m
AHWR071*	271,869	7,128,508	570	RC	67	-60	161					NSR
AHWR072*	271,902	7,128,483	570	RC	71	-60	130	73	81	8	1.8	8m @ 1.8g/t Au from 73m
AHWR073*	271,921	7,128,427	571	RC	71	-60	130	63	72	9	2.2	9m @ 2.2g/t Au from 63m
AHWR074*	271,733	7,129,247	569	RC	71	-60	80	52	57	5	0.4	5m @ 0.4g/t Au from 52m
and								61	63	2	9.3	2m @ 9.3g/t Au from 61m
AHWR075*	271,705	7,129,237	569	RC	71	-60	120					NSR
AHWR101*	271,879	7,128,456	570	RC	63	-60	127					NSR
AHWR102*	271,939	7,128,562	570	RC	69	-61	49	0	1	1	0.3	1m @ 0.3g/t Au from 0m
and								9	23	14	1.2	14m @ 1.2g/t Au from 9m
and								27	43	16	0.8	16m @ 0.8g/t Au from 27m
AHWR103*	271,913	7,128,552	570	RC	73	-61	79	22	44	22	0.7	22m @ 0.7g/t Au from 22m
and								60	64	4	1.5	4m @ 1.5g/t Au from 60m
AHWR104*	271,829	7,128,612	569	RC	67	-61	157	103	107	4	1.6	4m @ 1.6g/t Au from 103m, incl. 1m @ 5.2g/t Au
including								106	107	1	5.2	
and								144	145	1	1.9	
AHWR105*	271,804	7,128,603	570	RC	67	-61	199					NSR
AHWR106*	271,884	7,128,717	569	RC	71	-61	109	72	73	1	1.8	1m @ 1.8g/t Au from 72m
and								77	78	1	0.3	1m @ 0.3g/t Au from 77m
and								99	109	10	1.5	10m @ 1.5g/t Au from 99m to BOH
HWRC064*	271,726	7,129,129	568	RC	71	-60	99	89	99	10	24.3	10m @ 24.3g/t Au from 89m to BOH
HWRC065*	271,821	7,129,163	568	RC	253	-58	117	92	93	1	0.9	1m @ 0.9g/t Au from 92m
and								96	98	2	0.7	2m @ 0.7g/t Au from 96m
and								101	102	1	0.4	1m @ 0.4g/t Au from 101m
HWRC078*	271,752	7,129,136	568	RC	75	-60	100	51	52	1	0.7	1m @ 0.7g/t Au from 51m
and								78	80	2	0.9	2m @ 0.9g/t Au from 78m
HWRC079*	271,708	7,129,122	568	RC	75	-59	150	105	106	1	0.5	1m @ 0.5g/t Au from 105m
and								110	117	7	1.2	7m @ 1.2g/t Au from 110m
HWRC080*	271,787	7,129,177	568	RC	72	-61	102					NSR
HWRC081*	271,768	7,129,171	568	RC	72	-62	111					NSR
HWRC082*	271,744	7,129,162	568	RC	72	-61	105	68	69	1	1.2	1m @ 1.2g/t Au from 68m
HWRC083*	271,721	7,129,155	568	RC	74	-60	111	22	23	1	2.4	1m @ 2.4g/t Au from 22m
and								81	92	11	5.3	11m @ 5.3g/t Au from 81m
HWRC084*	271,697	7,129,146	568	RC	75	-61	123	113	123	10	0.8	10m @ 0.8g/t Au from 113m to BOH

For personal use only





Hole ID	Coordinates (MGA94 Zone 51)			Hole Details				Intercept Details				
	Easting (m)	Northing (m)	RL (m)	Hole Type	Azi (deg)	Dip (deg)	Total Depth (m)	Depth from (m)	Depth To (m)	Intercept Width (m)	Grade (g/t)	Grade Summary/ Comments
HWRC085*	271,675	7,129,141	568	RC	73	-60	110	100	101	1	0.8	1m @ 0.8g/t Au from 100m
and								103	104	1	1.0	1m @ 1g/t Au from 103m
HWRC086*	271,808	7,129,132	568	RC	74	-60	99	81	82	1	2.1	1m @ 2.1g/t Au from 81m
HWRC087*	271,786	7,129,124	568	RC	72	-60	99					NSR
HWRC088*	271,764	7,129,116	568	RC	70	-60	105	52	67	15	2.6	15m @ 2.6g/t Au from 52m, incl. 4m @ 8.2g/t Au
including								57	61	4	8.2	
HWRC089*	271,735	7,129,108	568	RC	75	-59	117	71	72	1	0.4	1m @ 0.4g/t Au from 71m
and								83	89	6	3.4	6m @ 3.4g/t Au from 83m
HWRC090*	271,711	7,129,102	568	RC	71	-60	123	59	60	1	4.6	1m @ 4.6g/t Au from 59m
HWRC106*	271,755	7,129,190	568	RC	74	-60	99	31	32	1	0.7	1m @ 0.7g/t Au from 31m
HWRC107*	271,737	7,129,186	568	RC	74	-60	105	68	69	1	0.5	1m @ 0.5g/t Au from 68m
HWRC108*	271,711	7,129,177	568	RC	72	-60	117	16	17	1	1.1	1m @ 1.1g/t Au from 16m
and								58	62	4	0.4	4m @ 0.4g/t Au from 58m
HWRC109*	271,789	7,129,100	568	RC	73	-59	99					NSR
HWRC110*	271,766	7,129,092	568	RC	73	-59	99	68	69	1	0.3	1m @ 0.3g/t Au from 68m
HWRC111*	271,743	7,129,083	568	RC	74	-59	105	85	86	1	0.5	1m @ 0.5g/t Au from 85m
and								89	90	1	1.2	1m @ 1.2g/t Au from 89m
HWRC238*	271,673	7,129,115	568	RC	73	-60	240	116	119	3	2.9	3m @ 2.9g/t Au from 116m
and								164	167	3	0.3	3m @ 0.3g/t Au from 164m
and								171	172	1	0.6	1m @ 0.6g/t Au from 171m
HWRC241*	271,682	7,129,170	568	RC	71	-61	227	50	53	3	0.3	3m @ 0.3g/t Au from 50m
and								62	63	1	0.3	1m @ 0.3g/t Au from 62m
and								64	65	1	0.3	1m @ 0.3g/t Au from 64m
and								130	133	3	0.6	3m @ 0.6g/t Au from 130m
HWRC242*	271,735	7,129,030	568	RC	72	-61	250	93	95	2	1.2	2m @ 1.2g/t Au from 93m
and								221	223	2	0.3	2m @ 0.3g/t Au from 221m
HWAC1774*	271,550	7,129,200	572	AC	270	-60	54					NSR
HWAC1775*	271,600	7,129,200	572	AC	270	-60	63					NSR
HWAC1776*	271,650	7,129,200	572	AC	270	-60	65					NSR
HWAC1777*	271,700	7,129,200	572	AC	270	-60	57					NSR
HWAC1778*	271,750	7,129,200	572	AC	270	-60	78					NSR
HWAC1779*	271,800	7,129,200	572	AC	270	-60	68					NSR
HWAC1780*	271,850	7,129,200	572	AC	270	-60	74					NSR
HWAC1781*	271,900	7,129,200	572	AC	270	-60	81					NSR
HWAC1782*	271,950	7,129,200	572	AC	270	-60	89	20	24	4	0.4	4m @ 0.4g/t Au from 20m
HWAC1791*	271,700	7,129,000	572	AC	270	-60	13					NSR
HWAC1792*	271,750	7,129,000	572	AC	270	-60	57					NSR

For personal use only



Hole ID	Coordinates (MGA94 Zone 51)			Hole Details				Intercept Details				
	Easting (m)	Northing (m)	RL (m)	Hole Type	Azi (deg)	Dip (deg)	Total Depth (m)	Depth from (m)	Depth To (m)	Intercept Width (m)	Grade (g/t)	Grade Summary/ Comments
HWAC1793*	271,800	7,129,000	572	AC	270	-60	64					NSR
HWAC1794*	271,850	7,129,000	572	AC	270	-60	75	64	68	4	1.0	4m @ 1g/t Au from 64m
HWAC1795*	271,900	7,129,000	572	AC	270	-60	65					NSR
HWAC1796*	271,950	7,129,000	572	AC	270	-60	70					NSR
HWAC1797*	272,000	7,129,000	572	AC	270	-60	80					NSR
HWAC1806*	271,800	7,128,800	572	AC	270	-60	48					NSR
HWAC1807*	271,850	7,128,800	572	AC	270	-60	56					NSR
HWAC1808*	271,900	7,128,800	572	AC	270	-60	64					NSR
HWAC1809*	271,950	7,128,800	572	AC	270	-60	87	24	60	36	1.2	36m @ 1.2g/t Au from 24m, incl. 16m @ 2.5g/t Au
including								32	48	16	2.5	
HWAC1810*	272,000	7,128,800	572	AC	270	-60	69					NSR

\*Previously announced or historic result

A cutoff of 0.3g/t Au was applied to each significant intercept.

For personal use only



## Appendix B

### JORC Table 1 – Warmblood – Palomino

#### Section 1 Sampling Techniques and Data

Criteria	JORC Code explanation	Commentary
<p>Sampling techniques</p>	<ul style="list-style-type: none"> <li>• <i>Nature and quality of sampling (eg cut channels, random chips, or specific specialised industry standard measurement tools appropriate to the minerals under investigation, such as down hole gamma sondes, or handheld XRF instruments, etc). These examples should not be taken as limiting the broad meaning of sampling.</i></li> <li>• <i>Include reference to measures taken to ensure sample representivity and the appropriate calibration of any measurement tools or systems used.</i></li> <li>• <i>Aspects of the determination of mineralisation that are Material to the Public Report.</i></li> <li>• <i>In cases where 'industry standard' work has been done this would be relatively simple (eg 'reverse circulation drilling was used to obtain 1 m samples from which 3 kg was pulverised to produce a 30 g charge for fire assay'). In other cases more explanation may be required, such as where there is coarse gold that has inherent sampling problems. Unusual commodities or mineralisation types (eg submarine nodules) may warrant disclosure of detailed information.</i></li> </ul>	<p><b><u>Alloy Resources</u></b></p> <p>The Warmblood prospect was first discovered by Alloy Resources Ltd in 2011 (please refer to ASX announcements 9 June 2011 &amp; 22 June 2011), with the completion of 101 air core holes, testing extensions to the Filly SW prospect returning significant oxide gold mineralisation.</p> <p>Aircore drilling was completed by Raglan Drilling and were completed to blade refusal, usually at saprock or fresh bedrock to an average depth of 66 metres.</p> <p>This reconnaissance drilling was carried out a widely spaced pattern of 200 metres by 400 metres, with drill samples composited over 4 metre intervals and assays for gold down to 0.001ppm or 1ppb Au. Any gold values greater than 0.05ppm Au in the 4 metre composite were considered to be significant warrant follow up drilling.</p> <p>Drilling samples were transported by trailer to Wiluna, were they were placed in bulka bags and shipped to Perth via Toll-Ipec for assay. The drilling samples were analysed by ALS-Chemex in Perth. All samples and blind standards were analysed for gold using 30g fire assay and ICP-AES finish (range 0.001-10ppm Au). Assays greater than 10ppm were analysed using the AA25 methos, but only standard samples were above this level.</p> <p>The initial RC program at Warmblood was carried out by Easternwell Drilling. RC samples were split directly from the cyclone into 2kg bags for every metre drilled. Samples were assayed as 4 metre composites. For all 4 metre composite samples which returned greater than 0.5g/t Au, 1 metre samples were collected from the original 'split' one metre samples and assayed.</p>

For personal use only



For personal use only

Criteria	JORC Code explanation	Commentary
		<p><b>Alloy Resources &amp; Doray Minerals Ltd (JV)</b></p> <p>From 2013 to 2021 exploration work was undertaken by Alloy Resources and Doray Minerals Ltd under the pre-existing JV agreement. The details regarding RC sampling from this work is outlined below:</p> <ul style="list-style-type: none"><li>• Reverse circulation (RC) percussion drill chips collected through a cyclone and cone splitter at 1m intervals.</li><li>• Spitter was cleaned regularly during drilling.</li><li>• Splitter was cleaned and levelled at the end of each hole.</li><li>• Mineralisation determined qualitatively through rock type, sulphide and quartz content and intensity of alteration.</li><li>• Mineralisation determined quantitatively via assay (aqua-regia digest followed by ICP-MS for multi-element data and 25g Fire Assay and AAS determination for gold at 1m intervals). RC samples pulverized to 75 µm</li><li>• All samples analysed by aqua-regia digest followed by ICP-MS for multi-element data and 25g Fire Assay and AAS determination for gold at 1 m intervals.</li></ul> <p><b><u>Strickland Metals Ltd</u></b></p> <p><b>Diamond Drilling</b></p> <ul style="list-style-type: none"><li>• Diamond coring was undertaken predominantly as HQ sizing, with PQ utilized to maximise recovery, where required, particularly within saprolite and clay zones.</li><li>• Triple-tubing was utilised throughout to maximise recovery.</li><li>• Diamond core samples were collected at geologically-defined intervals, with a minimum sample length of 0.5m and a maximum of 1.2m.</li></ul>



For personal use only

Criteria	JORC Code explanation	Commentary
		<ul style="list-style-type: none"><li>• Core samples were cut using an automated variable-speed diamond saw with half core, weighing approximately 3kg, submitted for analysis.</li><li>• OREAS certified reference material (CRM) was inserted at a ratio of 1:20 throughout sampling. The grade ranges of the CRMs were selected based on grade populations and economic grade ranges. The reference material type was selected based on the geology, weathering, and analysis method of the sample.</li><li>• Density measurements were collected as per Water Displacement Method 3 (Lipton, 2001) with paraffin wax coatings used for oxide and porous samples. Selected core samples were 0.1 – 0.2 m in size. Aluminium cylinders of 0.1 and 0.2 m in length, with known mass and density were measured at regular intervals at a ratio of 1:20, as a reference material. Duplicate sample weights were measured in fresh rock at a ratio of 1:20.</li><li>• Handheld instruments, such as an Olympus Vanta pXRF and Terraplus KT-10 meter were used to aid geological interpretation. CRMs were tested at regular intervals at a ratio of 1:20.</li></ul> <p><b>RC Drilling</b></p> <ul style="list-style-type: none"><li>• 2-3 kg samples were split from dry 1 m bulk samples. The sample was initially collected from the cyclone in an inline collection box, with independent upper and lower shutters. Once the full metre was drilled to completion, the drill bit was lifted off the bottom of the hole, creating a gap between samples; ensuring the entirety of the 1 m sample was collected, and over-drilling did not occur. When the gap of air entered the collection box, the top shutter was closed off. Once the top shutter was closed, the bottom shutter was opened, dropping the sample under gravity over a cone splitter.</li><li>• Two even 2 – 3 kg duplicate sample splits, from the A- and B-chutes of the splitter, were collected at the same time for each metre, with the remaining reject bulk sample being collected in labelled green bags directly below the cyclone, minimising external contamination.</li></ul>



For personal use only

Criteria	JORC Code explanation	Commentary
		<ul style="list-style-type: none"><li>• Original sample bags were consistently collected from the A-chute, whilst duplicate sample splits were collected from the B-chute. During the sample collection process, the original and duplicate calico sample splits, and green bag of bulk reject sample were weighed to test for sample splitting bias and sample recovery.</li><li>• Green bags were then placed in neat lines on the ground, with tops folded over to avoid contamination. Duplicate B-chute sample bags are retained and stored on site for follow up analysis and test work.</li><li>• In mineralised zones, the original A-chute sample split was sent to the laboratory for analysis. In non-mineralised 'waste' zones, a 4 m composite scoop sample was collected from the green bags and the A-chute bag retained on site for follow up analysis test work. All composite intervals over 0.1 g/t Au were resampled at 1 m intervals using the original A-chute bag from the cyclone splitter.</li><li>• QA samples were inserted at a combined ratio of 1:20 throughout. Field duplicates were collected at a 1:40 ratio from the B-chute of the cone splitter at the same time as the original sample was collected from the A-chute. OREAS certified reference material (CRM) was inserted at a ratio of 1:40. The grade ranges of the CRMs were selected based on grade populations and economic grade ranges. The reference material type was selected based on the geology, weathering, and analysis method of the sample.</li><li>• The cyclone was cleaned after each rod, at the base of oxidation, and when deemed necessary by the geologist to minimise contamination of samples. Sample condition was recorded for bias analysis. The cyclone was balanced at the start of each rod and checked after each sample to avoid split bias. Dual air-vibrators on the cyclone transfer box were utilised, when necessary, to aid sample throughput. Vibrators were placed on opposite</li></ul>



For personal use only

Criteria	JORC Code explanation	Commentary
		<p>sides of the cyclone and perpendicular to the chutes to avoid vibration-induced splitting bias.</p> <ul style="list-style-type: none"> <li>Handheld instruments, such as an Olympus Vanta pXRF and Terraplus KT-10 meter were used to aid geological interpretation. CRMs were tested at regular intervals at a ratio of 1:20.</li> </ul>
<p>Drilling techniques</p>	<ul style="list-style-type: none"> <li>Drill type (eg core, reverse circulation, open-hole hammer, rotary air blast, auger, Bangka, sonic, etc) and details (eg core diameter, triple or standard tube, depth of diamond tails, face-sampling bit or other type, whether core is oriented and if so, by what method, etc).</li> </ul>	<p><b>Historic Drilling</b></p> <ul style="list-style-type: none"> <li>The original Eagle Mining RAB program was completed by Kennedy Drilling.</li> <li>Eagle Mining engaged with Drillex to undertake the Reverse Circulation drilling.</li> </ul> <p>In 2019 Alloy Resources undertook Reverse Circulation Drilling with an 120mm bit.</p> <p><b>Strickland Metals Ltd</b></p> <p><b>Diamond Drilling</b></p> <ul style="list-style-type: none"> <li>Diamond Drilling was undertaken by Terra Drilling using a truck-mounted KWL1600 drill rig.</li> <li>Diamond coring was undertaken predominantly as HQ sizing, with PQ utilised to maximise recoveries where necessary. Triple-tubing was utilised to maximise recovery.</li> <li>REFLEX Sprint IQ and OMNI-Tool North-Seeking Gyroscopes were used for downhole dip and azimuth calculation, with multishot measurements taken every 30m during drilling, and a continuous IN and OUT readings taken at end-of-hole (EOH).</li> <li>REFLEX TN-14 Rig Aligner was used to align the rig to within 0.01 degrees of the planned azimuth, dip and roll at the start of each hole.</li> <li>Boart Longyear Orientation tools were used for core orientation.</li> </ul>



For personal use only

Criteria	JORC Code explanation	Commentary
		<p><b>RC Drilling</b></p> <ul style="list-style-type: none"> <li>• RC drilling was undertaken by Ranger Drilling and Red Rock Drilling:               <ul style="list-style-type: none"> <li>○ Ranger Drilling: using a truck-mounted Hydco 350RC Rig with a 1350 cfm @ 500 psi on-board compressor, a 1150 cfm onboard Booster, and a truck-mounted Sullair 900 cfm @ 350 psi Auxiliary Compressor.</li> <li>○ Red Rock Drilling: a truck mounted Hydco 40 350RC Rig with a 1050 cfm @ 350 psi on-board compressor and a truck mounted Air Research Bootser (2410).</li> </ul> </li> <li>• RC holes were drilled with a 5 ½” hammer.</li> <li>• REFLEX Sprint IQ and OMNI-Tool North-Seeking Gyroscopes were used for downhole dip and azimuth calculation, with multishot measurements taken every 30m during drilling, and a continuous IN and OUT readings taken at end-of-hole (EOH).</li> <li>• RELFEX TN-14 Rig Aligner was used to align the rig to within 0.01 degrees of the planned azimuth, dip and roll at the start of each hole.</li> </ul>
<p>Drill sample recovery</p>	<ul style="list-style-type: none"> <li>• <i>Method of recording and assessing core and chip sample recoveries and results assessed.</i></li> <li>• <i>Measures taken to maximise sample recovery and ensure representative nature of the samples.</i></li> <li>• <i>Whether a relationship exists between sample recovery and grade and whether sample bias may have occurred due to preferential loss/gain of fine/coarse material.</i></li> </ul>	<p><b>Strickland Metals Ltd</b></p> <p><b>Diamond Drilling</b></p> <ul style="list-style-type: none"> <li>• Diamond core samples are considered dry.</li> <li>• Triple-tubing and the appropriate drill tube diameter was selected (PQ, HQ, or NQ) depending on ground competency to maximise sample recovery.</li> <li>• Sample recovery is recorded every run (average run length of 3m) and is generally above 98%, except for in very broken ground.</li> <li>• Core was cut in half, with the same half of the core submitted to the laboratory for analysis.</li> </ul>





For personal use only

Criteria	JORC Code explanation	Commentary
		<ul style="list-style-type: none"> <li>From the collection of recovery data, no identifiable bias exists.</li> </ul> <p><b>RC Drilling</b></p> <ul style="list-style-type: none"> <li>During the RC sample collection process, the original and duplicate cone split samples, and green bag reject bulk samples were weighed to test for bias and sample recoveries. The majority of this work was undertaken in ore zones.</li> <li>Once drilling reached fresh rock, a fine mist of water was used to suppress dust and limit loss of fines through the cyclone chimney.</li> <li>At the end of each metre, the bit was lifted off the bottom of hole to separate each metre drilled.</li> <li>The majority of samples were of good quality, with ground water having minimal effect on sample quality or recovery.</li> <li>From the collection of recovery data, no identifiable bias exists.</li> </ul> <p><b>Historic Drilling</b></p> <ul style="list-style-type: none"> <li>RC drill chip recoveries recorded at the time of logging and stored in the database.</li> <li>Sample splitter was cleaned at the end of each rod to ensure no sample hang-ups have occurred. Sample bag weights are recorded and in general were approximately 3kg.</li> <li>Wet samples due to excess ground water were noted when present.</li> </ul> <p>As sample recoveries were generally very high, there is no known relationship between sample recovery and grade.</p>
Logging	<ul style="list-style-type: none"> <li>Whether core and chip samples have been geologically and geotechnically logged to a level of detail to support appropriate Mineral Resource estimation, mining studies and metallurgical studies.</li> </ul>	<p><b>Strickland Metals Ltd</b></p> <ul style="list-style-type: none"> <li>Logging of lithology, structure, alteration, veining, mineralisation, oxidation state, weathering, mineralogy, colour, magnetic susceptibility and pXRF geochemistry were recorded.</li> </ul>



For personal use only

Criteria	JORC Code explanation	Commentary
	<ul style="list-style-type: none"> <li>• Whether logging is qualitative or quantitative in nature. Core (or costean, channel, etc) photography.</li> <li>• The total length and percentage of the relevant intersections logged.</li> </ul>	<ul style="list-style-type: none"> <li>• Logging was both qualitative and quantitative in nature.</li> </ul> <p><b>Diamond Drilling</b></p> <ul style="list-style-type: none"> <li>• Diamond core was geotechnically logged at 1cm resolution; recording recovery, RQD, orientation confidence, joint density, joint sets, joint asperity and fill mineralogy.</li> <li>• Core trays were photographed wet and dry.</li> <li>• Structural measurements were collected utilizing the IMDEX IQ-Logger 2, with reference measurements taken at the start of each logging session and every 20 measurements throughout the drill hole to ensure instrument calibration and data quality.</li> </ul> <p><b>RC Drilling</b></p> <ul style="list-style-type: none"> <li>• RC chips were washed, logged and a representative sub-sample of the 1 m drill sample retained in reference chip trays for the entire length of a hole.</li> <li>• Reference chip trays were photographed wet and dry.</li> </ul> <p><b>Historic Drilling</b></p> <ul style="list-style-type: none"> <li>• Aircore holes were logged qualitatively and chip trays photographs were taken across all metre intervals.</li> <li>• RC Holes were logged to a level of detail to support future mineral resource estimation: lithology; alteration; mineralization; geotechnical (Diamond core only); structural.</li> <li>• Qualitative: lithology, alteration, foliation</li> <li>• Quantitative: vein percentage; mineralization (sulphide) percentage;</li> <li>• All holes logged for the entire length of hole.</li> </ul> <p>All RC holes were chipped and archived.</p>



For personal use only

Criteria	JORC Code explanation	Commentary
<p><i>Sub-sampling techniques and sample preparation</i></p>	<ul style="list-style-type: none"> <li><i>If core, whether cut or sawn and whether quarter, half or all core taken.</i></li> <li><i>If non-core, whether riffled, tube sampled, rotary split, etc and whether sampled wet or dry.</i></li> <li><i>For all sample types, the nature, quality and appropriateness of the sample preparation technique.</i></li> <li><i>Quality control procedures adopted for all sub-sampling stages to maximise representivity of samples.</i></li> <li><i>Measures taken to ensure that the sampling is representative of the in situ material collected, including for instance results for field duplicate/second-half sampling.</i></li> <li><i>Whether sample sizes are appropriate to the grain size of the material being sampled.</i></li> </ul>	<p><b><u>Strickland Metals Ltd</u></b></p> <p><b>Diamond Drilling</b></p> <ul style="list-style-type: none"> <li>Diamond core samples were collected at geologically defined intervals, with a minimum sample length of 0.5m and maximum of 1.2m.</li> <li>Samples were cut using an automated variable-speed diamond saw.</li> <li>Core was cut in half, with the same half of the core submitted to the laboratory for analysis.</li> <li>Diamond core samples are considered dry.</li> <li>Triple-tubing and the appropriate drill tube diameter was selected (PQ, HQ, or NQ) depending on ground competency to maximise sample recovery.</li> <li>Sample recovery is recorded every run (average run length of 3m) and is generally above 98%, except for in very broken ground.</li> <li>Handheld instruments, such as an Olympus Vanta pXRF and Terraplug KT-10 Magnetic Susceptibility meter, were used to aid geological interpretation. Core was analysed at 1m intervals for 60 seconds (3 x 20 second beams) utilising an Olympus Vanta pXRF instrument. CRMs were tested at regular intervals at a ratio of 1:20.</li> </ul> <p><b>RC Drilling</b></p> <ul style="list-style-type: none"> <li>RC samples were split from dry, 1m bulk sample via a cone splitter directly from the cyclone.</li> <li>Weighing of calico and reject green samples to determine sample recovery compared to theoretical sample recovery, and check sample bias through the splitter.</li> <li>Field duplicates collected from the B-chute of the splitter through the entire hole at the same time as the original sample collection from the A-chute.</li> </ul>



For personal use only

Criteria	JORC Code explanation	Commentary																
		<p data-bbox="1182 288 1482 312"><b>Quality Control Procedures</b></p> <ul data-bbox="1182 339 2042 603" style="list-style-type: none"><li data-bbox="1182 339 2042 464">Approximately 3kg of sample was submitted to ALS, Perth WA for analysis via 50g fire assay with an ICP-AES finish (method code: Au-ICP22). Samples that over-ranged are subsequently analysed by 50g fire assay and gravimetric finish (method code: Au-GRA22).</li><li data-bbox="1182 491 2042 547">Ore zones were additionally analysed via 250g Photon Assay (method code: Au-PA01).</li><li data-bbox="1182 574 1626 603">Detection limits of utilised methods:</li></ul> <table border="1" data-bbox="1361 624 1933 868"><thead><tr><th>Method</th><th>Unit</th><th>Lower Limit</th><th>Upper Limit</th></tr></thead><tbody><tr><td>Au-ICP22</td><td>ppm</td><td>0.001</td><td>10</td></tr><tr><td>Au-GRA22</td><td>ppm</td><td>0.01</td><td>100</td></tr><tr><td>Au-PA01</td><td>ppm</td><td>0.03</td><td>350</td></tr></tbody></table> <ul data-bbox="1182 879 2042 1358" style="list-style-type: none"><li data-bbox="1182 879 2042 935">Sample duplicates (DUP) were inserted at a ratio of 1:20 throughout sampling of ore zones, and 1:40 throughout sampling of waste material.</li><li data-bbox="1182 962 2042 1150">OREAS certified reference material (CRM) was inserted at a ratio of 1:20 throughout sampling of ore zones, and 1:40 throughout sampling of waste material. The grade ranges of the CRMs were selected based on grade populations and economic grade ranges. The reference material type was selected based on the geology, weathering, and analysis method of the sample.</li><li data-bbox="1182 1177 2042 1270">The total combined QAQC (DUPs and CRMs) to sample ratio through ore zone material was 1:10. For waste zones the combined QAQC to sample ratio was 1:20.</li><li data-bbox="1182 1297 2042 1358">Field Duplicates and CRMs were submitted to the lab using unique Sample IDs.</li></ul>	Method	Unit	Lower Limit	Upper Limit	Au-ICP22	ppm	0.001	10	Au-GRA22	ppm	0.01	100	Au-PA01	ppm	0.03	350
Method	Unit	Lower Limit	Upper Limit															
Au-ICP22	ppm	0.001	10															
Au-GRA22	ppm	0.01	100															
Au-PA01	ppm	0.03	350															



For personal use only

Criteria	JORC Code explanation	Commentary
		<ul style="list-style-type: none"><li>• For Fire Assay, all samples were sorted, dried at 105°C and weighed prior to crushing to 2mm. Crushed samples were then split and pulverised to 75µm, with a QC specification of ensuring &gt;85% passing &lt; 75µm. 50g of pulverised sample was then analysed for Au by fire assay and ICP-AES (low-grade) or gravimetric (ore-grade) finish.</li><li>• Sample size and preparation is appropriate for the grain size of the sample material.</li></ul> <p><b>Historic Alloy Resources RC Drilling</b></p> <ul style="list-style-type: none"><li>• RC chips were cone split every metre, sampled dry where possible and wet when excess ground water could not be prevented. Sample condition (wet, dry or damp) was recorded at the time of logging.</li><li>• Where mineralization was unlikely, the samples were composited by spear sampling – four x 1 metre subsamples combined to approximately 3kg and submitted for assay.</li><li>• The entire ~3kg RC sample was pulverised to 75µm (85% passing). This is considered best practice and is standard throughout the industry.</li><li>• Pulp duplicates taken at the pulverizing stage and selective repeats conducted at the laboratories discretion.</li><li>• Duplicate samples were taken every 50<sup>th</sup> sample.</li><li>• Sample size is appropriate for the grain size of the sample material.</li></ul> <p><b>Historic Pulp Multi Element Assay</b></p> <ul style="list-style-type: none"><li>• Historic pulp samples from Warmblood were stored at the STK warehouse in sealed cardboard boxes that were labelled with the key lab job number from the historic gold only Fire Assay analysis. The lab job number was referenced with the existing drill database to determine each representative hole ID. The samples/holes requiring multi-element analysis were then subsequently placed in new cardboard boxes with new sample</li></ul>



For personal use only

Criteria	JORC Code explanation	Commentary
		<p>submission numbers and sent to ALS laboratory in Perth for full four-acid multi element analysis – code MS61.</p>
<p>Quality of assay data and laboratory tests</p>	<ul style="list-style-type: none"> <li><i>The nature, quality and appropriateness of the assaying and laboratory procedures used and whether the technique is considered partial or total.</i></li> <li><i>For geophysical tools, spectrometers, handheld XRF instruments, etc, the parameters used in determining the analysis including instrument make and model, reading times, calibrations factors applied and their derivation, etc.</i></li> <li><i>Nature of quality control procedures adopted (eg standards, blanks, duplicates, external laboratory checks) and whether acceptable levels of accuracy (ie lack of bias) and precision have been established.</i></li> </ul>	<p><b><u>Strickland Metals Ltd</u></b></p> <p><b>Diamond Drilling</b></p> <ul style="list-style-type: none"> <li>Sample duplicates (DUP) were inserted at a ratio of 1:20 throughout sampling of ore zones, and 1:40 throughout sampling of waste material.</li> <li>OREAS certified reference material (CRM) was inserted at a ratio of 1:20 throughout sampling of ore zones, and 1:40 throughout sampling of waste material. The grade ranges of the CRMs were selected based on grade populations and economic grade ranges. The reference material type was selected based on the geology, weathering, and analysis method of the sample.</li> <li>The total combined QAQC (DUPs and CRMs) to sample ratio through ore zone material was 1:10. For waste zones the combined QAQC to sample ratio was 1:20.</li> <li>Field Duplicates and CRMs were submitted to the lab using unique Sample IDs.</li> <li>ALS, Perth WA conduct CRM analysis and laboratory check assays at a combined ratio of 1:25 samples as part of standard laboratory QAQC protocols.</li> <li>Blank quartz ‘flushes’ were inserted into the sample sequence throughout high-grade ore zones. After each high-grade sample (usually determined by the presence of visible gold) is crushed, a quartz flush is crushed. A second quartz flush is run after each sample is pulverised, prior to the quartz crush flush undergoing pulverisation. In total, two quartz flushes are conducted (one for each preparation stage) for each suspected high-grade sample to determine the level of potential contamination across samples.</li> <li>No bias or contamination is seen across samples.</li> </ul>



For personal use only

Criteria	JORC Code explanation	Commentary
		<ul style="list-style-type: none"><li>• Core was analysed at 1m intervals for 60 seconds (3 x 20 second beams) utilising an Olympus Vanta pXRF instrument. CRMs were tested at regular intervals at a ratio of 1:20. Olympus Vanta pXRF instruments cannot accurately measure elemental Au and whole-suite elemental data are not considered appropriate for reporting. pXRF data are used as a guide for logging only.</li></ul> <p><b>RC Drilling</b></p> <ul style="list-style-type: none"><li>• 2-3 kg samples were split from dry 1 m bulk samples. The sample was initially collected from the cyclone in an inline collection box, with independent upper and lower shutters. Once the full metre was drilled to completion, the drill bit was lifted off the bottom of the hole, creating a gap between samples; ensuring the entirety of the 1 m sample was collected, and over-drilling did not occur. When the gap of air entered the collection box, the top shutter was closed off. Once the top shutter was closed, the bottom shutter was opened, dropping the sample under gravity over a cone splitter.</li><li>• Two even 2 – 3 kg duplicate sample splits, from the A- and B-chutes of the splitter, were collected at the same time for each metre, with the remaining reject bulk sample being collected in labelled green bags directly below the cyclone, minimising external contamination.</li><li>• Original sample bags were consistently collected from the A-chute, whilst duplicate sample splits were collected from the B-chute. During the sample collection process, the original and duplicate calico sample splits, and green bag of bulk reject sample were weighed to test for sample splitting bias and sample recovery.</li><li>• Green bags were then placed in neat lines on the ground, with tops folded over to avoid contamination. Duplicate B-chute sample bags are retained and stored on site for follow up analysis and test work.</li><li>• In mineralised zones, the original A-chute sample split was sent to the laboratory for analysis. In non-mineralised 'waste' zones, a 4 m composite</li></ul>



For personal use only

Criteria	JORC Code explanation	Commentary
		<p>scoop sample was collected from the green bags and the A-chute bag retained on site for follow up analysis test work. All composite intervals over 0.1 g/t Au were resampled at 1 m intervals using the original A-chute bag from the cyclone splitter.</p> <ul style="list-style-type: none"><li>• QA samples were inserted at a combined ratio of 1:20 throughout. Field duplicates were collected at a 1:40 ratio from the B-chute of the cone splitter at the same time as the original sample was collected from the A-chute. OREAS certified reference material (CRM) was inserted at a ratio of 1:40. The grade ranges of the CRMs were selected based on grade populations and economic grade ranges. The reference material type was selected based on the geology, weathering, and analysis method of the sample.</li><li>• The cyclone was cleaned after each rod, at the base of oxidation, and when deemed necessary by the geologist to minimise contamination of samples. Sample condition was recorded for bias analysis. The cyclone was balanced at the start of each rod and checked after each sample to avoid split bias. Dual air-vibrators on the cyclone transfer box were utilised, when necessary, to aid sample throughput. Vibrators were placed on opposite sides of the cyclone and perpendicular to the chutes to avoid vibration-induced splitting bias.</li><li>• Handheld instruments, such as an Olympus Vanta pXRF and Terraplus KT-10 meter were used to aid geological interpretation. CRMs were tested at regular intervals at a ratio of 1:20.</li></ul> <p><b><u>Historic Eagle Mining Drilling</u></b></p> <ul style="list-style-type: none"><li>• Samples were analysed for Au by single stage mix and grind preparation, with an aqua-regia digest and AAS finish to 0.02ppm. Repeats (approximately 10%) were fire assays to a detection limit of 0.01ppm. All samples were sent to Australian Assay Laboratories (AAL) in Boulder, WA.</li></ul>





For personal use only

Criteria	JORC Code explanation	Commentary
		<p><b>Historic Alloy Resources RC Drilling</b></p> <ul style="list-style-type: none"> <li>• Fire assay was used and is a total digest technique.</li> <li>• Certified reference material standards, 1 in every 50 samples.</li> <li>• Blanks: a lab barren quartz flush is requested following a predicted high-grade sample (i.e., visible gold).</li> <li>• Lab: Random pulp duplicates were taken on average 1 in every 10 samples.</li> </ul> <p>Accuracy and precision levels have been determined to be satisfactory after analysis of these QAQC samples.</p>
<p>Verification of sampling and assaying</p>	<ul style="list-style-type: none"> <li>• <i>The verification of significant intersections by either independent or alternative company personnel.</i></li> <li>• <i>The use of twinned holes.</i></li> <li>• <i>Documentation of primary data, data entry procedures, data verification, data storage (physical and electronic) protocols.</i></li> <li>• <i>Discuss any adjustment to assay data.</i></li> </ul>	<p><b>Strickland Metals Ltd</b></p> <ul style="list-style-type: none"> <li>• Logging and sampling were recorded directly into LogChief, utilising lookup tables and in-file validations, on a Toughbook by a geologist at the rig.</li> <li>• Logs and sampling were imported daily into Micromine for further validation and geological confirmation.</li> <li>• When received, assay results were plotted on section and verified against neighboring drill holes.</li> <li>• From time to time, assays will be repeated if they fail company QAQC protocols.</li> <li>• All data is verified by senior Company geologists.</li> <li>• No adjustments to assay data are made.</li> </ul> <p><b>Historic Alloy Resources RC Drilling</b></p> <ul style="list-style-type: none"> <li>• All sampling was routinely inspected by senior geological staff. Significant intercepts were inspected by senior geological staff.</li> <li>• No twinned holes were drilled during the program.</li> </ul>



For personal use only

Criteria	JORC Code explanation	Commentary
		<ul style="list-style-type: none"> <li>Data was hard keyed into Excel data capture software and merged with Datashed SQL based database on internal company server. Data is validated by a Database Administrator, import validation protocols in place.</li> <li>Visual checks of data was completed within Surpac software by consultant geologists.</li> <li>No adjustments were made to any of the assay data.</li> </ul> <p>This data is now managed and hosted by Mitchell River Group.</p>
<p>Location of data points</p>	<ul style="list-style-type: none"> <li>Accuracy and quality of surveys used to locate drill holes (collar and down-hole surveys), trenches, mine workings and other locations used in Mineral Resource estimation.</li> <li>Specification of the grid system used.</li> <li>Quality and adequacy of topographic control.</li> </ul>	<p><b><u>Strickland Metals Ltd</u></b></p> <ul style="list-style-type: none"> <li>The grid system used was MGA94 Zone 51 and drillhole collar positions surveyed using a Garmin GPSMAP 64 (+/- 3m accuracy).</li> <li>REFLEX Sprint IQ and OMNI-Tool North-Seeking Gyroscopes were used for downhole dip and azimuth calculation, with multishot measurements taken every 30m during drilling, and a continuous IN and OUT readings taken at end-of-hole (EOH).</li> <li>RELIFEX TN-14 Rig Aligner was used to align the rig to within 0.01 degrees of the planned azimuth, dip and roll at the start of each hole.</li> </ul> <p>Boart Longyear Orientation tools were used for core orientation.</p> <p><b><u>Historic Alloy Resources RC Drilling</u></b></p> <ul style="list-style-type: none"> <li>Collars: surveyed with GPS with expected relative accuracy of approximately 2-3m.</li> <li>Downhole: surveyed with in-rod reflex Gyro tool continuously.</li> <li>Holes are located in MGA94 zone 51.</li> <li>Estimated RL's were assigned during the drilling.</li> </ul> <p>Strickland has engaged with an independent surveyor to pick up and locate all collars that have not been subject to a DGPS pick-up.</p>



For personal use only

Criteria	JORC Code explanation	Commentary
<p><i>Data spacing and distribution</i></p>	<ul style="list-style-type: none"> <li>• <i>Data spacing for reporting of Exploration Results.</i></li> <li>• <i>Whether the data spacing and distribution is sufficient to establish the degree of geological and grade continuity appropriate for the Mineral Resource and Ore Reserve estimation procedure(s) and classifications applied.</i></li> <li>• <i>Whether sample compositing has been applied.</i></li> </ul>	<p><b>Historic Drilling</b></p> <ul style="list-style-type: none"> <li>• Holes were drilled on a variable collar spacing of approximately 40m across the bulk of the Palomino resource estimate with up to 80 to 100 metre spacings in the northern part (down-plunge extent) of Palomino.</li> <li>• Intercepts are reported as composites of individual 1m assay results from a cut-off of 0.5g/t Au.</li> <li>• Reported intercepts include internal waste averaging 3m.</li> </ul> <p><b>Strickland Metals Ltd</b></p> <ul style="list-style-type: none"> <li>• Diamond Drilling and RC drilling at Warmblood is located between existing 40m-spaced historical drill holes, extensional holes follow the sample spacing configuration of 40m x 40m.</li> <li>• Diamond and RC drilling at Marwari was completed on a 40m x 40m grid.</li> <li>• Diamond drilling at Bronco was typically completed on 40m spacing, with some holes completed at 40m x 20m.</li> <li>• Assay results show good continuity of grade and width of intercepts between STK and Historic drill holes, both along strike, down-dip and down-plunge.</li> <li>• The data spacing and distribution is sufficient to demonstrate spatial and grade continuity of the mineralised horizon to support the classification of the Mineral Resources reported.</li> <li>• Intercepts are reported as composites of individual 1m assay results from a cut-off of 0.5g/t Au.</li> </ul> <p>Reported intercepts include internal waste averaging 3m.</p>
<p><i>Orientation of data in relation</i></p>	<ul style="list-style-type: none"> <li>• <i>Whether the orientation of sampling achieves unbiased sampling of possible structures and the extent to which this is known, considering the deposit type.</i></li> </ul>	<ul style="list-style-type: none"> <li>• Based on the drilling completed to date, the orientation (both dip and plunge) of mineralisation is based on numerical Au assay values and</li> </ul>



For personal use only

Criteria	JORC Code explanation	Commentary
<p>to geological structure</p>	<ul style="list-style-type: none"> <li>If the relationship between the drilling orientation and the orientation of key mineralised structures is considered to have introduced a sampling bias, this should be assessed and reported if material.</li> </ul>	<p>confirmed by structural data collected from Strickland Metals' diamond drilling.</p> <ul style="list-style-type: none"> <li>The orientation of primary mineralisation is approximately vertical. Oxide mineralisation is approximately flat. STK-drilling has been completed at -60 degrees and perpendicular to the strike of mineralisation to avoid the introduction of bias to results.</li> <li>Drilling intercepts are reported as down-hole width.</li> </ul>
<p>Sample security</p>	<ul style="list-style-type: none"> <li>The measures taken to ensure sample security.</li> </ul>	<p><b><u>Strickland Metals Ltd</u></b></p> <ul style="list-style-type: none"> <li>Chain of Custody of digital data was managed by Strickland Metals Ltd.</li> <li>All samples were bagged in tied numbered calico bags, grouped into larger polyweave bags and cabled-tied. Polyweave bags were placed into larger Bulky Bags with a sample submission sheet and tied shut. Delivery address details were written on the side of the bag.</li> <li>Sample material was stored on site and, when necessary, delivered to the assay laboratory by Strickland Metals personnel and a nominated courier (DFS).</li> <li>Thereafter, laboratory samples were controlled by the nominated laboratory.</li> <li>Sample collection was controlled by digital sample control files and hard-copy ticket books.</li> </ul> <p><b><u>Historic Drilling</u></b></p> <ul style="list-style-type: none"> <li>The data was originally maintained by Eagle Mining Corporation and forwarded to Normandy Jundee Operation</li> <li>All DRM historic samples were selected, cut and bagged in a tied numbered calico bag, grouped into larger polyweave bags and cable tied. Polyweave bags were placed into larger Bulky Bags with a sample submission Doray Minerals Ltd, 21st October 2015 Criteria JORC Code explanation</li> </ul>



For personal use only

Criteria	JORC Code explanation	Commentary
		<p>Commentary sheet and tied shut. Consignment note and delivery address details were written on the side of the bag and delivered to Toll Express in Meekatharra. The bags were delivered directly to MinAnalytical in Canning Vale, WA who are NATA accredited for compliance with ISO/IEC17025:2005.</p> <ul style="list-style-type: none"> <li>All Alloy Resources historic samples were assayed by ALS Laboratories (Perth) using Aqua Regia (2012 AC program) and Fire Assay with ICP_MS finish (RC programs) to detection limits of 0.01 and 0.001ppm respectively.</li> </ul>
Audits or reviews	<ul style="list-style-type: none"> <li>The results of any audits or reviews of sampling techniques and data.</li> </ul>	<p><b>Strickland Metals</b></p> <ul style="list-style-type: none"> <li>All assay data is audited and reviewed by Mitchell River Group (MRG), with weekly performance meetings held between Strickland Personnel and the Database Manager at MRG.</li> <li>The multi-element geochemistry from the historic drill pulps was reviewed by Dr Nigel Brand (Geochemical Services Pty Ltd), who determined the key pathfinder element suite.</li> </ul> <p><b>Historic Drilling</b></p> <ul style="list-style-type: none"> <li>Performance meetings held between a DRM and MinAnalytical representative were conducted monthly. QAQC data were reviewed with each assay batch returned, and on regular monthly intervals (trend analysis).</li> </ul>

## Section 2: Reporting of Exploration Results

Criteria	JORC Code explanation	Commentary
Mineral tenement and land tenure status	<ul style="list-style-type: none"> <li>Type, reference name/number, location and ownership including agreements or material issues with third parties such as joint ventures, partnerships, overriding royalties, native title interests, historical sites, wilderness or national park and environmental settings.</li> </ul>	<ul style="list-style-type: none"> <li>Warmblood and Palomino are located on 100% owned STK tenure (tenement ID) E69/1772.</li> <li>L11 Capital Pty Ltd holds a 1% gross revenue royalty over the above tenure.</li> </ul>



Criteria	JORC Code explanation	Commentary
	<ul style="list-style-type: none"> <li>The security of the tenure held at the time of reporting along with any known impediments to obtaining a licence to operate in the area.</li> </ul>	
Exploration done by other parties	<ul style="list-style-type: none"> <li>Acknowledgment and appraisal of exploration by other parties.</li> </ul>	<ul style="list-style-type: none"> <li>Exploration prior to Strickland in the region was conducted by Eagle Mining and Great Central Mines Ltd. Drilling included shallow RAB and RC drilling that was completed in the mid – 1990s, all of which had been sampled, assayed, and logged and records held by the Company. This early work, including aeromagnetic data interpretation, was focused on gold and provided anomalous samples which was the focus of this period of exploration.</li> </ul>
Geology	<ul style="list-style-type: none"> <li>Deposit type, geological setting and style of mineralisation.</li> </ul>	<ul style="list-style-type: none"> <li>Palomino and Warmblood are Archean aged gold prospects with common host rocks and structures related to mesothermal orogenic gold mineralisation as found throughout the Yilgarn Craton of Western Australia.</li> </ul>
Drill hole Information	<ul style="list-style-type: none"> <li>A summary of all information material to the understanding of the exploration results including a tabulation of the following information for all Material drill holes:               <ul style="list-style-type: none"> <li>easting and northing of the drill hole collar</li> <li>elevation or RL (Reduced Level – elevation above sea level in metres) of the drill hole collar</li> <li>dip and azimuth of the hole</li> <li>down hole length and interception depth</li> <li>hole length.</li> </ul> </li> <li>If the exclusion of this information is justified on the basis that the information is not Material and this exclusion does not detract from the understanding of the report, the Competent Person should clearly explain why this is the case.</li> </ul>	<ul style="list-style-type: none"> <li>Historic gold intercepts have been compiled, with a summary of all information documented in Appendix A – Table 1, Table 2 and Table 3.</li> <li>Historic drill holes relating to the re-assay of existing pulps for multi-element pathfinder geochemistry.</li> </ul>
Data aggregation methods	<ul style="list-style-type: none"> <li>In reporting Exploration Results, weighting averaging techniques, maximum and/or minimum grade truncations (eg cutting of high grades) and cut-off grades are usually Material and should be stated.</li> <li>Where aggregate intercepts incorporate short lengths of high grade results and longer lengths of low grade results, the procedure used for such</li> </ul>	<ul style="list-style-type: none"> <li>No top-cuts have been applied when reporting results.</li> <li>A cut-off of 0.3g/t Au was applied for all significant gold assay results.</li> <li>The following values were deemed anomalous for the key pathfinder element suite associated with the gold mineralisation at Warmblood:</li> </ul>

For personal use only



Criteria	JORC Code explanation	Commentary
	<p>aggregation should be stated and some typical examples of such aggregations should be shown in detail.</p> <ul style="list-style-type: none"> <li>The assumptions used for any reporting of metal equivalent values should be clearly stated.</li> </ul>	<ul style="list-style-type: none"> <li>&gt;0.5ppm Te</li> <li>&gt;0.4ppm Bi</li> <li>&gt;10ppm W</li> <li>&gt;0.4ppm Ag</li> </ul>
Relationship between mineralisation widths and intercept lengths	<ul style="list-style-type: none"> <li>These relationships are particularly important in the reporting of Exploration Results.</li> <li>If the geometry of the mineralisation with respect to the drill hole angle is known, its nature should be reported.</li> <li>If it is not known and only the down hole lengths are reported, there should be a clear statement to this effect (eg 'down hole length, true width not known').</li> </ul>	<ul style="list-style-type: none"> <li>The orientation of primary mineralisation is approximately vertical. Oxide mineralisation is approximately flat. STK-drilling has been completed at -60 degrees and perpendicular to the strike of mineralisation to avoid the introduction of bias to results. Drilling intercepts are reported as down-hole width.</li> </ul>
Diagrams	<ul style="list-style-type: none"> <li>Appropriate maps and sections (with scales) and tabulations of intercepts should be included for any significant discovery being reported These should include, but not be limited to a plan view of drill hole collar locations and appropriate sectional views.</li> </ul>	<ul style="list-style-type: none"> <li>Please refer to the main body of text.</li> </ul>
Balanced reporting	<ul style="list-style-type: none"> <li>Where comprehensive reporting of all Exploration Results is not practicable, representative reporting of both low and high grades and/or widths should be practiced to avoid misleading reporting of Exploration Results.</li> </ul>	<ul style="list-style-type: none"> <li>All Au assays are presented in the appendix to this announcement for clarity. Representative higher-grade intervals have been presented in the text and section.</li> </ul>
Other substantive exploration data	<ul style="list-style-type: none"> <li>Other exploration data, if meaningful and material, should be reported including (but not limited to): geological observations; geophysical survey results; geochemical survey results; bulk samples – size and method of treatment; metallurgical test results; bulk density, groundwater, geotechnical and rock characteristics; potential deleterious or contaminating substances.</li> </ul>	<ul style="list-style-type: none"> <li>All meaningful and material information has been included in the body of the text.</li> <li>In March 2020, Alloy Resources engaged with Australian Laboratory Services (ALS) to undertake Metallurgical Testwork on Palomino RC chip samples. From the samples received, six composites were generated. Overall gold recovery, via gravity-amalgam and cyanide leaching at a 75um grind was high, at 89.03% and 87.2% respectively.</li> </ul>
Further work	<ul style="list-style-type: none"> <li>The nature and scale of planned further work (eg tests for lateral extensions or depth extensions or large-scale step-out drilling).</li> </ul>	<ul style="list-style-type: none"> <li>Continued RC and diamond drilling along strike and down plunge to determine the overall economic potential of each target area.</li> </ul>



Criteria	JORC Code explanation	Commentary
	<ul style="list-style-type: none"><li data-bbox="293 288 1155 379">• <i>Diagrams clearly highlighting the areas of possible extensions, including the main geological interpretations and future drilling areas, provided this information is not commercially sensitive.</i></li></ul>	

For personal use only