

Wide High-Grade Tin at Queen Hill Deposit Heemskirk

17.0m @ 1.79% Sn zone, wider and higher grade than resource model HIGHLIGHTS:

- Diamond drilling underway at the Heemskirk Tin Project in Tasmania is targeting the Severn and Queen Hill deposits upgrading Inferred resources to the Indicated category and testing for extensions to the 2023 Mineral Resource Estimate (MRE)¹.
- At the Queen Hill deposit, drillhole ZQ170 has returned multiple high-grade zones of mineralisation downhole including:
 - 4.75m @ 1.17% Sn from 163.45m
 - o **1.25m @ 2.52% Sn** from 191m
 - o **17.0m @ 1.79% Sn** from 203.8m including;
 - o **7.9m @ 2.74% Sn** from 206m, and includes,
 - o **1.5m @ 6.08% Sn** from 212m
 - o 2.05m @ 1.76% Sn from 226m
 - o 2.00m @ 1.88% Sn from 288m
- Drillhole ZQ170 targeted a zone of Indicated mineralisation to provide drill sample for metallurgical testing with the resulting intersection being wider than the existing resource model.
- The zone also contains high grade zinc, lead and silver mineralisation with an interval of 1.25m containing **18.1% Zn, 17.6% Pb and 379g/t Ag** from 212.65m depth.
- Mineralisation remains open down dip/plunge, and a deeper hole (ZQ173) is currently in progress testing for extensions at depth.
- Exploration holes on the northern end of the deposit confirm the system is open to the north.
- **Down hole electromagnetic (DHEM)** survey to commence on the margins of the deposit in December as part of the resource expansion program.
- A total of 9 holes for 4340 metres have been completed to date of the planned 24 hole 9,500m drill program, as part of the prefeasibility study (**PFS**) now underway.

¹ SRZ ASX Announcement 4 September 2023 – Heemskirk Tin Project MRE Update



Stellar's Managing Director Mr Simon Taylor commented:

"Drilling at Heemskirk continues to deliver outstanding results with the first hole from Queen Hill ZQ170 returning multiple zones of high-grade tin mineralisation down hole. The hole was designed to test a zone of Indicated mineralisation to provide drill sample for metallurgical testing and it is pleasing that the resulting intersection is wider than the existing geological model.

"We have immediately drilled a follow up hole ZQ173 chasing mineralisation at depth within an Inferred area of the resource model. Hole ZQ167 drilled to the north confirms the system is open and we will test this area and others with a downhole electromagnetic survey in December. We have utilised one of the three rigs to clean out historical holes over the past week at both Severn and Queen Hill for DHEM testwork as part of our resource expansion program.

"We look forward to providing further updates on prefeasibility activities, including drilling results, ore sorting and metallurgical results, as they come to hand."

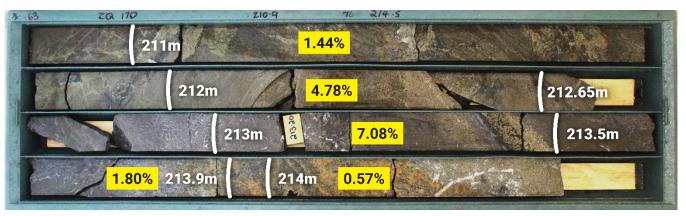


Figure 1: Diamond drill core from Severn hole ZQ170 from approximately 211m – 214.5m. Core shows broad massive pyrite with associated massive sphalerite-galena zone, interpreted to be replacing dolomite protolith. The zone returned high grade zinc-lead-silver mineralisation including **1.2m at 18.13% Zn, 17.61%Pb and 379g/t Ag** from 212.65m. Sn assays are shown in yellow as % Sn and depth intervals downhole in metres shown in white.

Stellar Resources Limited (ASX: SRZ, "Stellar" or the "Company") is pleased to report first drilling results from the Queen Hill deposit at its Heemskirk Tin Project ("**Heemskirk"**) in Western Tasmania. The program comprises a 24-hole (~9,500m) diamond drilling campaign focused on infill and extensional drilling. This release reports assay results from three holes drilled at Queen Hill (ZQ167, ZQ169 and ZQ170).

To date, Stellar has completed 9 holes for a total of 4340 metres. The Company has three rigs operating at present and will report further assays as they come to hand.

Refer to Figures 2 - 4 for drillhole cross sections and locations and Tables 1 – 2 for significant intersections and drill hole location data.



Queen Hill Infill - Holes ZQ167, 169 and 170

At Queen Hill, **Drillhole ZQ170** targeted the southern end of the Mineral resource model close to the Indicated and Inferred resource boundary. The hole was designed to target a zone of Indicated mineralisation to provide drill sample for metallurgical testing with the resulting intersection being wider than anticipated in the existing resource model.

The hole was highly successful returning multiple zones of high-grade mineralisation downhole including:

- 4.75m @ 1.17% Sn from 163.45m
- 2.10m @ 0.73% Sn from 166.1m
- **1.20m @ 0.54% Sn** from 181.6m
- 1.25m @ 2.52% Sn from 191m
- 17.0 @ 1.79% Sn from 203.8m including;
 - o **7.9m @ 2.74% Sn** from 206m, and includes,
 - o **3.90m @ 3.34% Sn** from 210m and includes,
 - **1.5m @ 6.08% Sn** from 212m
- 2.05m @ 1.76% Sn from 226m
- 2.00m @ 1.88% Sn from 288m
- **0.85m @ 1.87% Sn** from 302.15m

Mineralisation remains open down dip/plunge and a deeper hole (ZQ173) is currently in progress testing for an extensions at depth. ZQ173 was completed to a depth of 406m before a hole failure. A wedge off the hole is now underway to extend the hole.

Interestingly the zone also contains high grade zinc, lead and silver mineralisation with an interval of 1.25m containing **18.1% Zn, 17.6% Pb and 379g/t Ag from** 212.65m depth. Diamond core from this zone shows broad massive pyrite with associated massive sphalerite-galena, interpreted to be replacing dolomite protolith.

Holes ZQ167 and ZQ169 were also drilled at Queen Hill as exploration holes on the northern end of the deposit. ZQ167 hit minor mineralisation near the expected depths confirming the system is open to the north. Results included:

- **1.00m @ 0.42% Sn** from 157m
- **1.20m @ 0.41% Sn** from 232m
- 0.30m @ 0.69% Sn from 336.5m

5th December 2024



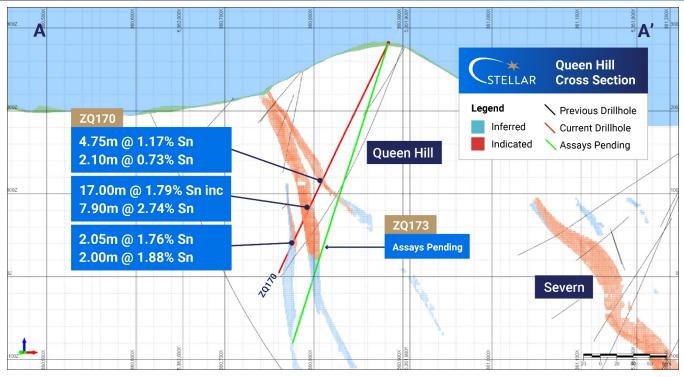


Figure 2: Drill Hole Cross Section A-A' (Located on figure 4), new drill holes ZQ170 and ZQ173, Indicated and Inferred resource blocks from the 2023 MRE¹

Table 1 – Summary of Significant Intercepts							
Hole ID	From	Width	Sn %	Cu %	Zn %	Pb %	Ag (g/t)
	157.00	1.00	0.42	0.02			
ZQ167	232.00	1.20	0.41	0.25			
	336.50	0.30	0.69	0.00			
ZQ169	No Significa	nt Intercepts					
ZQ170	163.45	4.75	1.17	0.86			
	166.10	2.10	0.73	0.03			
	181.60	1.20	0.54	0.01			
	191.00	1.25	2.52	0.02			
	203.80	17.00	1.79	0.03			
including	206.00	7.90	2.74	0.05			
including	210.00	3.90	3.34	0.06			
including	212.00	1.50	6.08	0.07			
including	212.65	1.25			18.13	17.61	379
	226.00	2.05	1.76	0.02			
	288.00	2.00	1.88	0.01			
	302.15	0.85	1.87	0.01			

Table 1 0 nifi. + Int

Calculated using a 0.40% Sn lower cut off and no more than 2 metres of internal dilution. Drillhole ZQ170 intersected mineralization at ~ 42 degrees to the modelled dip of the ore body. Hence the true widths are 67% or ~2/3 of the reported interval widths.

Stellar Resources Limited | ASX: SRZ | ABN: 96 108 758 961 Level 5, 56 Pitt Street, Sydney NSW 2000, Australia T: +61 2 8823 3179 | E: srzinfo@stellarresources.com.au

5th December 2024

For personal use only



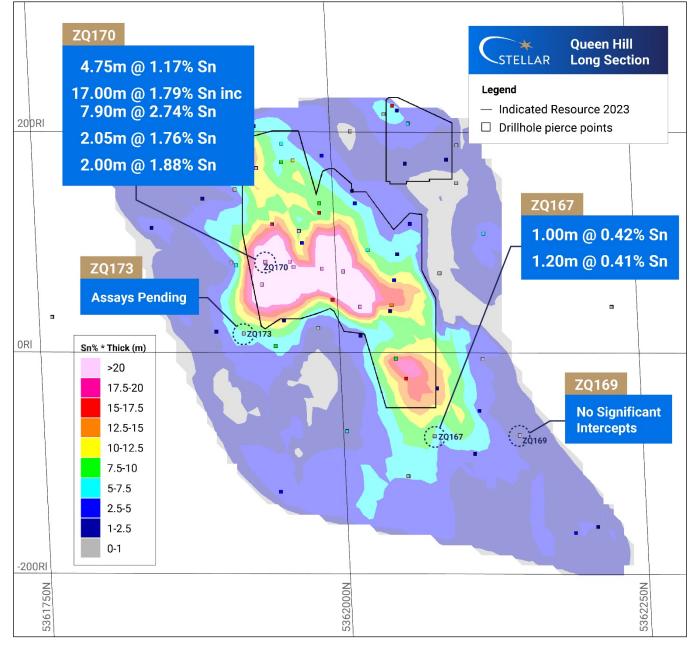


Figure 3: Queen Hill Long Section looking west showing Sept 2023 Severn Mineral Resource as projected total of the multiple mineralised resource zones and drillhole pierce points coloured by Sn% * Thickness (historic holes & SRZ holes shown). GDA Z55

5th December 2024



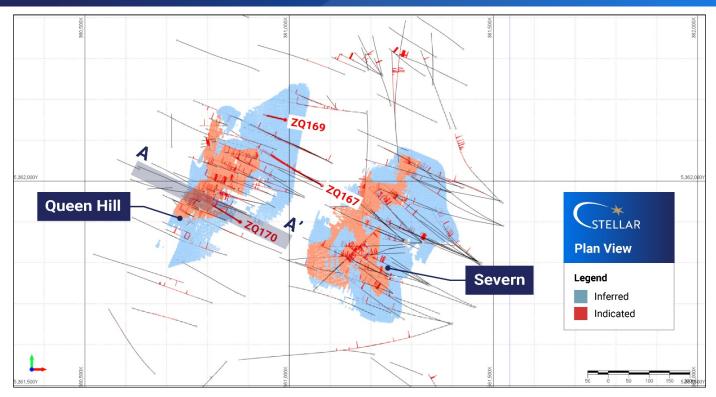


Figure 4: Drill hole location plan, location of cross section A-A' for Queen Hill holes ZQ167, ZQ169 and ZQ170 (Figure 2), highlighted in red. Blue box indicates section line and width of sectional view.

Further Work Programs and Drilling Progress

Drilling to date has completed 9 of the planned 24 holes with three rigs currently operating. A total of 4340 metres has been drilled, inclusive of two abandoned holes.

The drilling program is designed to advance Heemskirk to development ready status by providing key technical inputs for the Prefeasibility Study, while also aiming for mineral resource expansion by providing a DHEM platform to support further exploration drilling.

During the past two weeks one rig has been allocated to cleaning out of drill holes around the margin of the deposits and PVC casing of them to enable them to be utilised for DHEM surveys during December. The DHEM surveys will provide the opportunity to discover continuations or offsets on mineralised zones around the existing MRE.

Prefeasibility study work is underway with the commencement of metallurgical testwork, including the further trial of ore sorting on ore samples.

- ENDS -

5th December 2024



This announcement is authorised for release to the market by the Board of Directors of Stellar Resources Limited.

For further details please contact:

Simon Taylor Managing Director & CEO Stellar Resources Limited T: 0409 367 460 E: simon@stellarresources.com.au

For broker and media enquiries:

Jason Mack

Communications Advisor White Noise Communications **T:** +61 400 643 799 **E:** jason@whitenoisecomms.com

Competent Persons Statement

The information in this announcement that relates to exploration results has been compiled by Mr. Andrew Boyd who is an Executive Director and shareholder of the Company. Mr. Boyd is a Member of the Australian Institute of Geologists and has sufficient experience which is relevant to the style of mineralisation and type of deposit under consideration and to the activity which they are undertaking to qualify as a Competent Person as defined in the 2012 Edition of the Australasian Code for Reporting of Exploration Results, Mineral Resources and Ore Reserves (the JORC Code). Mr. Boyd has reviewed the contents of this news release and consents to the inclusion in this announcement of exploration results in the form and context in which they appear.

Forward Looking Statements

This report may include forward-looking statements. Forward-looking statements include, but are not limited to, statements concerning Stellar Resources Limited's planned activities and other statements that are not historical facts. When used in this report, the words such as "could", "plan", "estimate", "expect", "intend", "may", "potential", "should" and similar expressions are forward-looking statements. In addition, summaries of Exploration Results and estimates of Mineral Resources and Ore Reserves could also be forward-looking statements. Although Stellar Resources Limited believes that its expectations reflected in these forward-looking statements are reasonable, such statements involve risks and uncertainties and no assurance can be given that actual results will be consistent with these forward-looking statements. The entity confirms that it is not aware of any new information or data that materially affects the information included in this announcement and that all material assumptions and technical parameters underpinning this announcement continue to apply and have not materially changed. Nothing in this report should be construed as either an offer to sell or a solicitation to buy or sell Stellar Resources Limited securities.



About Stellar Resources:

Stellar Resources (**ASX:SRZ**) is focused on developing its world class Heemskirk Tin Project located in the mining friendly jurisdiction of Zeehan, Western Tasmania. The Company has defined a substantial high-grade resource totalling **7.48Mt at 1.04% Sn, containing 77.87kt of tin¹.** This ranks the Heemskirk Project as the highest-grade undeveloped tin resource in Australia and third globally.

The focus for the Company is to complete exploration and resource drilling at the Heemskirk Project to further grow the resource and increase its confidence by upgrading of its resource classifications. Currently, a large proportion of the resource is classified in the indicated category totalling 3.52Mt at 1.05% Sn for 37kt of contained tin and with 3.96Mt at 1.03%Sn for 41kt of contained tin the Inferred category.

Stellar also made a major discovery at its North Scamander Project in September 2023, with a maiden exploration drillhole intersecting a significant new high-grade silver, tin, zinc, lead and Indium polymetallic discovery. The Company has also delineated multiple down hole conductions via DHEM and FLEM surveys, providing high priority follow up targets.

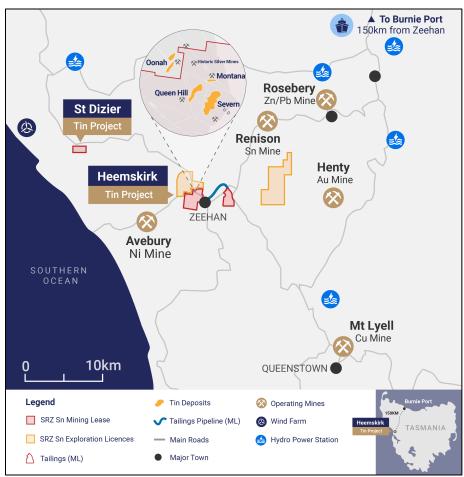


Figure 5 - Stellar Resources Heemskirk Tin Project Location

¹ SRZ ASX Announcement 4 September 2023 – Heemskirk Tin Project MRE Update. The Company confirms that it is not aware of any new information or data that materially affects the information included within the original announcement and that all material assumptions and technical parameters underpinning the MRE quoted in the release continue to apply and have not materially changed.

5th December 2024



Hole Number	Easting	Table 2 – Drill P Northing	RL	Depth	Azimuth	Dip
ZQ167	361080	5361990	203	388.3	299	-66
ZQ169	360990	5362150	231	406.2	283	-82
ZQ170	360880	5361900	282	308.7	302	-64

Notes:

All coordinates in Map Grid of Australia, Zone 55 (MGA Z55) Rounding errors may exist in length calculations



JORC Code, 2012 Edition – Table 1

Section 1: Sampling Techniques and Data (criteria in this section apply to all succeeding sections)

Criteria	JORC Code Explanation	Commentary
Sampling techniques	 Nature and Quality of sampling (e.g. cut channels, random chips or specific specialized industry standard measurement tools appropriate to the minerals under investigation, such as downhole gamma sondes, or handheld XRF instruments etc.). Include reference to measures taken to ensure sample representivity and the appropriate calibration of any measurement tools or systems used. Aspects of the determination of mineralisation that are Material to the Public Report. In cases where 'industry standard' work has been done this would be relatively simple (e.g. 'reverse circulation drilling was used to obtain 1m samples from which 3kg was pulverized to produce 30g charge for fire assay'). In other cases, more explanation may be required, such as where there is coarse gold that has inherent sampling problems. Unusual commodities or sampling types (e.g. submarine nodules) may warrant disclosure of detailed information. 	 The Zeehan Tin deposit has been delineated entirely by diamond drilling. Numerous drilling campaigns were completed between 1960 and 1992 by Placer, Gippsland, Minops, CRAE and Aberfoyle. Post 2010, diamond drilling was completed by Stellar with diamond core of nominally NQ or HQ diameter. Logged sulphide and siderite altered zones were selected for geochemical analysis. Approximately 1m samples of 2-3kg were taken from diamond saw cut drill core whilst respecting geological boundaries.
Drilling Techniques	• Drill type (e.g. core, reverse circulation, open hole hammer, rotary air blast, auger, bangka, sonic etc.) and details (e.g. core diameter, triple or standard tube, depth of diamond tails, face sampling bit or other type, where core is oriented and if so by what method, etc.)	All drill sampling by standard wireline diamond drilling.
Drill sample recovery	 Method of recording and assessing core and chip sample recoveries and results assessed. Measures taken to maximize sample recovery and ensure representative nature of the samples. Whether a relationship exists between sample recovery and grade and whether sample bias may have occurred due to preferential loss/gain of fine/coarse material 	 Core logging captured drilled recoveries and core loss. Recoveries generally excellent (95-100%) through mineralized sections.



Criteria	JORC Code Explanation	Commentary
Logging Sub- Sampling	 Whether core and chip samples have been geologically and geotechnically logged to a level of detail to support appropriate Mineral Resource estimation, mining studies and metallurgical studies. Whether logging is qualitative or quantitative in nature. Core (or costean, channel etc.) photography. The total length and percentage of the relevant intersections logged. If core, whether cut or sawn and whether quarter, half or all core taken. 	 Geological logging has been carried out on all holes by experienced geologists and technical staff. Holes logged for lithology, weathering, alteration, structural orientations, Geotech, RQD, magnetic susceptibility and mineralisation verified with an Olympus DPO 2000 pXRF. Photographed dry and wet prior to cutting. Logs loaded into excel spreadsheets and uploaded into access database. Standard lithology codes used for all drillholes. Half core split by diamond saw over 0.3 – 1.0m sample intervals while respecting geological contacts. Most
techniques and sample preparation	 If non-core, whether riffled, tube sampled, rotary split, etc. and whether sampled wet or dry For all sample types, the nature, quality and appropriateness of the sample preparation technique. Quality control procedures adopted for all sub sampling stages to maximize representivity of samples. Measures taken to ensure that the sampling is representative of the insitu material collected, including for instance results of field duplicate/second half sampling. Whether sample sizes are appropriate to the grain size of the material being sampled 	 sample intervals are 1.0m. Assay sample weights between 1 and 4kg are considered appropriate with respect to any coarse tin that may be present. Half core has specific gravity undertaken by the laboratory before it is coarse crushed and then pulverized to 85% passing 75um.
Quality of assay data and laboratory tests	 The nature, quality and appropriateness of the assaying and laboratory procedures used and whether the technique is considered partial or total. For geophysical tools, spectrometers, handheld XRF instruments, etc., the parameters used in determining the analysis including instrument make and model, reading times, calibration factors applied and their derivation etc. Nature of quality control procedures adopted (e.g. standards, blanks, duplicates, external laboratory checks) and whether acceptable levels of accuracy (i.e. lack of bias) and precision have been established. 	 Sn, Fe and S analyses were conducted at ALS Laboratories using a fused disc XRF technique (XRF15B). Fused disc XRF is considered a total technique, as it extracts and measures the whole of the element contained within the sample. Aqua regia acid digestion and multi element analysis using Induced coupled plasma mass spectrometry (ICP41a) for Sn, Li, Ag, Ba, Ca, Cr, Ga, La, Mo, P, Sb, Th, U, Zn, Al, Cu, Mg, Na, Pb, Sc, Ti, V, As, Bi, Co, Fe, K, Mn, Ni, Sr, Tl, W. Where required, overlimit ore grade base metals analysis is undertaken by Aqua regia acid digestion and multi element analysis using Induced coupled plasma mass spectrometry (ME-OG46). Where required, Pb that is overlimit for OG46Pb analysis, is analysed by a fused disc XRF technique (XRF15d). Certified reference material (CRM) are inserted approximately every 20 samples using custom made CRM material by OREAS with grades of ~ 0.3, 0.7 and 1.5% Sn Course blanks and fine blank OREAS 22e are also inserted after mineralised zones. Duplicate samples are requested approximately every 20 samples.



Criteria	JORC Code Explanation	Commentary
Verification of sampling and assaying	 The verification of significant intersections by either independent or alternative company personnel The use of twinned holes. Documentation of primary data, data entry procedures, data verification, data storage (physical and electronic) protocols. Discuss any adjustment to assay data. 	 Significant intersections were reviewed by company personnel. Eight twinned holes have been included in previous drilling program with six holes demonstrating moderate to high Sn grade variability between 20% and 50%. Two holes demonstrating extreme grade and or geological variability. Data is collected by qualified geologists and experienced field assistants and entered into excel spreadsheets. Data is imported into Microsoft access tables. Data is regularly backed up and archival copies of the database stored on the cloud and hard drives.
Location of data points	 Accuracy and quality of surveys used to locate drill holes (collar and downhole surveys) trenches, mine workings and other locations used in mineral resource estimation Specification of grid system used Quality and accuracy of topographic control. 	 Drill holes are sighted and initially recorded by hand held GPS (+/- 5m accuracy), with final locations picked up by a licensed surveyor on a 3 monthly basis. The holes reported in this release are located by handheld (non-RTK) GPS All Post 2010 drill collars surveyed by licensed surveyor using differential GPS, including those included in this announcement. Pre 2010 drill collars surveyed by licensed surveyor with the exception of 13 early drill holes located to within 1m by local grid tape and compass for Queen Hill deposit. Down hole surveys by downhole camera or Tropari. 2017 holes by Deviflex. For the 2021/2022 holes a digital magnetic survey tool used up to hole ZQ146. From hole Z1S43W onwards, a Devigyro survey tool and a DeviAlligner tool has been used. The Digital Terrain Model has been generated from lands department 10m contours and adjusted with surveyed drill collar and control points.
Data Spacing and distribution	 Data spacing for reporting Exploration Results Whether data spacing and distribution is sufficient to establish the degree of geological and grade continuity appropriate for the Mineral Resource and Ore Reserve estimation procedure(s) and classifications applied. Whether sample compositing has been applied 	 Drill hole spacing for this phase of exploration drilling is approximately 50m.
Orientation of data in relation to geological structure	 Whether the orientation of sampling achieves unbiased sampling of possible structures and the extent to which this is known, considering the deposit type. If the relationship between the drilling orientation and the orientation of key mineralised structures is considered to have introduced a sampling bias, this should be assessed and reported if material. 	 The majority of drill holes have been drilled local grid east west sub-perpendicular to the steeply east dipping mineralisation in the Severn and Queen Hill Deposits. Drillhole ZQ170 intersected at approximately 42° to the currently modelled dip of the ore body. Hence the (true) downhole interval lengths are 67% or ~2/3 of the interval widths in this announcement. Drill hole orientation is not considered to have introduced any material sampling bias.

5th December 2024



Criteria	JORC Code Explanation	Commentary
Sample Security	The measures taken to ensure sample security.	 Post 2010 chain of custody is managed by Stellar from the drill site to ALS laboratories in Burnie. All samples, bagged in pre-numbered calico bags and delivered in labelled poly-weave bags. Pre 2010 sample security is not documented.
Audits or Reviews	• The results of any audits or reviews of sampling techniques and data.	 No audits or reviews of sampling data and techniques have been completed.

Section 2: Reporting of Exploration Results (Criteria listed in the preceding section also apply to this section)

Criteria	JORC Code Explanation	Commentary
Mineral tenement and land tenure status	 Type, reference name/number, location and ownership including agreements or material issues with third parties such as joint ventures, partnerships, overriding royalties, native title interests, historical sites, wilderness or national park and environmental settings. The security of tenure held at the time of exercise scheme advantage. 	 ML2023P/M, RL5/1997 and EL13/2018 hosting the Heemskirk Tin Project in Western Tasmania are 100% owned by Stellar Resources Ltd.
	reporting along with known impediments to obtaining a license to operate the area	
Exploration done by other parties	 Acknowledgement and appraisal of exploration by other parties. 	 Early mining activity commenced in the 1880's with the production of Ag-Pb sulphides and Cu-Sn sulphides from fissure loads. Modern exploration commenced by Placer in the mid 1960's with the Queen Hill deposit discovered by Gippsland in 1971. The Aberfoyle-Gippsland JV explored the tenements until 1992 with the delineation of the Queen Hill, Severn and Montana deposits.
Geology	 Deposit type, geological setting and style of mineralization. 	 The Heemskirk Tin Deposits are granite related tin- sulphide-siderite vein and replacement style deposits hosted in the Oonah Formation and Crimson Creek Formation sediments and volcanics. Numerous Pb-Zn-Ag fissure lodes are associated with the periphery of the mineralizing system. Mineralisation is essentially stratabound controlled by northeast plunging fold structures associated with northwest trending faults. Tin is believed to be sourced from a granite intrusion located over 1km from surface below the deposit.



Criteria	JORC Code Explanation	Commentary
Drill hole information	 A summary of all information material to the understanding of the exploration results including a tabulation of the following information for all Material drill holes: easting and northing of the drill hole collar elevation or RL (Reduced Level - elevation above sea level in metres) of the drill hole collar dip and azimuth of the hole downhole length and interception depth hole length If the exclusion of this information is justified on the basis that the information is not Material and this exclusion does not detract from the understanding of the report, the Competent Person should clearly explain why this is the case 	See the body of this report for tabulated drill hole collar details and mineralised results.
Data aggregation methods	 In reporting of Exploration Results, weighting averaging techniques, maximum and/or minimum grade truncations (e.g. cutting of high grades) and cut-off grades are usually material and should be stated. Where aggregate intercepts include short lengths of high grade results and longer lengths of low grade results, the procedure used for aggregation should be stated and some examples of such aggregations should be shown in detail The assumptions used for any reporting of metal equivalent values should be clearly stated. 	 Exploration assay results are downhole length weighted averages for Sn%, Cu%. High grade intercepts may have been selected from some longer low-grade length weighted downhole average intercepts and presented as length-weighted average inclusions. No metal equivalents have been used.
Relationship between mineralisation widths and intercept lengths	 These relationships are particularly important in the reporting of Exploration Results. If the geometry of the mineralization with respect to the drill hole angle is known, its nature should be reported. If it is not known and only the downhole lengths are reported, there should be a clear statement to this effect (e.g. down hole length, true width not known) 	 Drillhole ZQ170 intersected at approximately 420 to the currently modelled dip of the ore body. Hence the (true) downhole interval lengths are 67% or ~2/3 of the interval widths in this announcement. Mineralisation is thought to be of a stockwork style with vein angles within mineralised zones variable.
Diagrams	 Appropriate maps and sections (with scales) and tabulated intercepts should be included for any significant discovery being reported. These should include, but not be limited to a plan view of drill collar locations and appropriate sectional views. 	See body of the announcement for relevant plan and sectional views.



Criteria	JORC Code Explanation	Commentary
Balanced reporting	 Where comprehensive reporting of all Exploration Results is not practicable, representative reporting of both low and high grades and/ or widths should be practiced to avoid misleading reporting of Exploration Results 	 In general, mineralised zones above a Sn cut off of 0.4% and greater than 3.0m length or shorter intervals with a SN% x m length of > 1.2%.m are included in the tables and figures associated with this report, however in some cases higher cut off grades have been used for selection of significant intervals.
Other substantive exploration data	 Other exploration data, if meaningful and material, should be reported including (but not limited to): geological observations; geophysical survey result; geochemical survey results; bulk samples – size and method of treatment; metallurgical test results; bulk density, groundwater, geotechnical and rock characteristics; potential deleterious or contaminating substances. 	 Metallurgical test work completed by ALS/BRL laboratories and supervised by Worley-Parsons over a number of different campaigns on drill core samples. Deposits have been zoned mineralogically and metallurgically Cassiterite is the dominant tin-bearing mineral occurring as free grains and in complex mineral composites. Grain sizes vary according to ore type, with Severn having the coarsest and Upper Queen Hill having the finest. Cassiterite liberation generally commences at a grind of 130 microns and is largely complete at 20 microns. Based on the work undertaken by ALS metallurgy, Stellar anticipates that concentrates grading approximately 48% tin at an overall tin recovery of 73% will be obtained from the Zeehan Tin ores. Bulk densities determined on mineralised intercepts using the Archimedes method.
Further work	 The nature and scale of planned further work (e.g. test for lateral extensions or depth extensions or large scale step out drilling). Diagrams clearly highlighting the areas of possible extensions, including the main geological interpretations and future drilling areas, provided this information is not commercially sensitive. 	 Prefeasibility level metallurgical and mining studies are occurring in conjunction with the current drilling. Environmental baseline studies are underway to support the application of a Notice of Intent with the Environmental Protection Authority of Tasmania. The mineral deposits remain open down dip and down plunge and will be explored as access becomes available with mine development.